

CEMENTITIOUS BARRIERS PARTNERSHIP

**Tc OXIDATION IN SLAG-BASED
SODIUM SALT WASTE FORMS EXPOSED TO
WATER AND MOIST HANFORD SOIL**

C. A. Langton
Savannah River National Laboratory
Savannah River Site
Aiken, South Carolina 29808

August, 2014

CBP-TR-2014-05, Rev. 0

ACKNOWLEDGEMENTS

This report was prepared for the United States Department of Energy under Interagency Agreement No. DE-AI09-09SR22667 and is an account of work performed under that contract. This report was also prepared with the financial support by the U. S. Department of Energy, under Cooperative Agreement Number DE-FC01-06EW07053 entitled 'The Consortium for Risk Evaluation with Stakeholder Participation III' awarded to Vanderbilt University. Reference herein to any specific commercial product, process, or service by trademark, name, manufacturer, or otherwise does not necessarily constitute or imply endorsement, recommendation, or favoring of same by Savannah River Nuclear Solutions, Vanderbilt University or by the United States Government or any agency thereof. The views and opinions of the authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof. This report is part of a larger multi-investigator project supported by the U. S. Department of Energy entitled the Cementitious Barriers Partnership. The opinions, findings, conclusions, or recommendations expressed herein are those of the authors and do not necessarily represent the views of the U.S. Department of Energy. This work was also partially supported by the National Institute of Standards and Technology Sustainable, High Performance Infrastructure Materials program.

DISCLAIMER

This work was prepared under an agreement with and funded by the U. S. Government. Neither the U.S. Government or its employees, nor any of its contractors, subcontractors or their employees, makes any express or implied: 1. warranty or assumes any legal liability for the accuracy, completeness, or for the use or results of such use of any information, product, or process disclosed; or 2. representation that such use or results of such use would not infringe privately owned rights; or 3. endorsement or recommendation of any specifically identified commercial product, process, or service. Any views and opinions of authors expressed in this work do not necessarily state or reflect those of the United States Government, or its contractors, or subcontractors.

**Printed in the United States of America
United States Department of Energy
Office of Environmental Management
Washington, DC**

**This document is available on the U.S. DOE Information Bridge and on the
CBP website: <http://cementbarriers.org/>
An electronic copy of this document is also available through links on the following**

SUMMARY

Cementitious materials are used to solidify and stabilize aqueous based radioactive waste containing sodium salts. The types and proportions of cementitious ingredients used to treat aqueous radioactive waste streams containing sodium salts depend on the performance objectives for the waste forms and the compositions of the waste streams.

Several U.S. DOE sites use or plan to use waste forms and/or concrete containment structures for radioactive waste disposal that are designed to have a chemically reducing environment to immobilize selected contaminants such as Tc(VII)O_4^- and Cr(VI)O_4^{2-} . These waste forms and containment structures are typically deployed in near surface unsaturated oxidizing environments. Consequently, the effect of exposure to air (oxygen) and water containing dissolved oxygen during production, during the period of institutional control, and over the long term period of performance is important for predicting the speciation and mobility of the redox sensitive radioactive and stable contaminants.

Both the SRS and Hanford waste streams contain soluble technetium which may require stabilization to meet disposal requirements. Technetium stabilization is a difficult problem because: 1) Tc is soluble and very mobile in the oxidized form (Tc(VII)O_4^-) typical of near surface environments, and 2) Tc-99 is a long-lived isotope with a half-life of 2.1×10^5 years which poses a great challenge to prediction performance and places demanding requirements on the engineered barriers and environment to meet current regulatory disposal requirements.

A depth-discrete sampling and leaching method approach for measuring contaminant oxidation rate (effective contaminant specific oxidation rate) was used in this study. The method was modified by coating all sides of a cylindrical sample with an impermeable epoxy and then cutting a fresh surface 2 to 2.5 cm from the original top surface to eliminate sample inhomogeneity as the result of settling as a reason from observed results and provides 1-D soluble ion transport and gas transport information.

Based on nitrate (assumed to 100 % soluble during curing and exposure and used as a reference) leaching results for the depth- discrete subsamples, regions depleted in nitrates were identified from the top surfaces to 9.5 and 3 mm into samples Tc2-9 (exposed to Hanford sediment) and Tc2-10 (DI water), respectively. Low mass fractions of nitrate were leached from these depth-discrete samples compared to samples further from the exposed surface presumably because a significant portion of the nitrate had already migrated into the soil or water, respectively. Depth-discrete subsample leaching results for Na can be interpreted in the same way over the same regions in the two samples tested.

Soluble Tc was leached from all of the depth-discrete subsamples from both Tc2-9 and Tc2-10 which strongly suggests that oxygen was present in the entire length of both samples. About 24 mass percent of the Tc in the original sample, was leached (soluble) from subsamples between 0.8 and 46 mm below the exposed surface of Tc2-9 (exposed to Hanford sediment). The same percent (24%) was leached from the subsamples between 0.8 and 11 mm below the exposed surface of Tc2-10 (exposed to DI water). This suggests that the rate of oxygen migration into the sample exposed to soil was faster than the rate of migration into the sample exposed to water which is consistent with the more rapid transport of ions through a gas phase as compared to a liquid phase. It was assumed that moisture in the Hanford sediment was not sufficient to completely block the surface pores with respect to gas transport across the soil-waste form boundary or to block the transport of gas as efficiently as DI water.

Additional data are required to fully understand and quantify the progression of the region depleted in soluble ions and the rate of oxygen ingress and oxidation of redox sensitive contaminants such as Tc. However, these scoping studies have provided insights to the multiple mechanisms affecting the solubility and leachability of redox sensitive contaminants.

In conclusion, leaching monolithic porous cementitious waste forms in water appears to be conservative for non-redox sensitive contaminants such as nitrate and sodium. However, leaching data obtained under saturated exposure conditions do not appear to be conservative for redox sensitive contaminants such as Tc(IV) phases which are easily and whose mobility is dependent on oxidation state. Leaching crushed samples in water still seems to be a conservative approach to estimating the concentrations of soluble contaminants in a waste form.

ABBREVIATIONS

1-D	One dimensional
ASTM	American Society of Testing and Materials
DI	Deionized (water)
DOE	United States Department of Energy
EPA	United States Environmental Protection Agency
GGBFS	Ground Granulated Blast Furnace Slag
HTWOS	(Hanford) Tank Waste Operations System
IC	Ion Chromatography
ICP-OES	Inductively Coupled Plasma Optical Emission Spectrometer
IDF	(Hanford) Integrated Disposal Facility
LAW	Low Activity Waste
M	Molar
PNNL	Pacific Northwest National Laboratory
RSD	Relative Standard Deviation
SRNL	Savannah River National Laboratory
SRS	Savannah River Site
TDS	Total Dissolved Solids
TT/QAP	Task Technical and Quality Assurance Plan
WPT	(Hanford) Waste Treatment and Immobilization Plant
w/cm	Water to cementitious materials ratio

TABLE OF CONTENTS

ACKNOWLEDGEMENTS.....	i
SUMMARY.....	ii
ABBREVIATIONS.....	iv
LIST OF TABLES.....	vi
LIST OF FIGURES.....	vii
INTRODUCTION.....	1
Objective	1
Background.....	1
EXPERIMENTAL METHOD.....	2
Waste Form Sample Preparation.....	2
Simulant	3
Cementitious reagents.....	3
Waste form	3
Waste Form Exposure Conditions	4
Waste Form Depth-Discrete Leaching.....	5
Fraction leached.....	5
RESULTS	6
Tc-99 Leaching.....	6
Nitrate and Sodium Leaching	10
CONCLUSIONS.....	14
REFERENCES	15
ATTACHMENT 1. CHARACTERIZATION OF AS_RECEIVED HANFORD SEDIMENT MOISTURE CONTENT AND SATURATED MOISTURE CONTENT.....	16
ATTACHMENT 2. ANALYTICAL RESULTS FOR SUBSAMPLE LEACHATES.....	19

LIST OF TABLES

Table 1. LAW 5 M Simulant based on Hanford Tank Waste Operations Simulator (HTWOS) modeling [9].....	2
Table 2. Ingredients and proportions of the 5 M Na simulant used to prepare the waste form.	3
Table 3. Tc-99 spike added to the HTWOS Average 5 M Na simulant [9].	3
Table 4. Ingredients in Tc Spiked waste forms.....	3
Table 5. Summary of curing and exposure times.	4
Table 6. Tc-99 leachate results for depth-discrete subsample cut from Sample Tc2-9 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.	8
Table 7. Tc-99 leachate results for depth-discrete subsample cut from Sample Tc2-10 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in DI water.....	9
Table 8. Na leachate results for depth discrete-subsample cut from Sample Tc2-9 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.	11
Table 9. NO ₃ ⁻ leachate results for depth discrete-subsample cut from Sample Tc2-9 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in DI water.....	11
Table 10. Na leachate results for depth-discrete subsample cut from Sample Tc2-10 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.	12
Table 11. NO ₃ ⁻ leachate results for depth-discrete subsample cut from Sample Tc2-10 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.	12
Table 12. Summary of NO ₃ ⁻ , Na, and Tc leached as a function of distance from top surface of TC2-9 (exposed to Hanford sediment) and Tc2-10 (exposed to DI water).	13
Table 13. Cation and anion leachate results for depth discrete subsample cut from Sample Tc2-9 cured at ambient temperature in a humid environment. The “fresh” top surface was subsequently exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture...	20
Table 14. Cation and anion leachate results for depth discrete subsample cut from Sample Tc2-10 cured at ambient temperature in a humid environment. A “fresh” surface was subsequently exposed to and leached in DI water.	24

LIST OF FIGURES

- Figure 1. Epoxy coated sample with uncoated top surface, soil leaching media before sample was covered with about 3 cm of additional sediment, and container during exposure. . 4
- Figure 2. Hanford sediment passing No. 18 sieve (left) and retained on No. 18 sieve (right). 5
- Figure 3. Percent Tc-99 leached from depth-discrete subsamples as a function of distance from the as cast sample illustrating that the top portion was removed in order to expose a “fresh” surface to unsaturated Hanford sediment and DI water. 6
- Figure 4. Percent Tc-99 leached from depth-discrete subsamples as a function of distance from fresh surfaces exposed to unsaturated Hanford sediment and DI water. 7
- Figure 5. Na, NO₃⁻, and Tc-99 percents leached from depth-discrete subsamples as a function of distance from fresh surfaces exposed to unsaturated Hanford sediment and DI water. 13

INTRODUCTION

Several U.S. DOE sites use or plan to use waste forms and/or concrete containment structures for radioactive waste disposal that are designed to have a chemically reducing environment to immobilize selected contaminants such as Tc(VII)O_4^- and Cr(VI)O_4^{2-} . These waste forms and containment structures are typically deployed in near surface unsaturated oxidizing environments. Consequently, the effect of exposure to air (oxygen) and water containing dissolved oxygen during production, during the period of institutional control, and over the long term period of performance is important for predicting the speciation and mobility of the redox sensitive radioactive and stable contaminants.

The rate of oxidation is important to the long-term performance of reducing salt waste forms because the solubility of some contaminants, e.g., technetium, is a function of oxidation state. TcO_4^- in the salt solution is reduced to Tc(IV) and has been shown to react with ingredients in the waste form to precipitate low solubility sulfide and/or oxide phases [1, 2, and 3]. Upon exposure to oxygen, the compounds containing Tc(IV) oxidize to the pertechnetate ion, Tc(VII)O_4^- , which is highly soluble in water and aqueous solutions. Consequently the rate of technetium oxidation front advancement into a monolith and the technetium leaching profile as a function of depth from an exposed surface are important to waste form performance and ground water concentration predictions. The rate of oxidation front advancement into a monolith and the effect of oxygen ingress on redox sensitive contaminants are needed to:

- 1) Develop the conceptual model for performance predictions,
- 2) Provide data to parameterize fate and transport models, and
- 3) Validate computational codes.

Objective

The objectives of this study were to: utilize depth-discrete sampling and zero head space leaching to explore the effect of exposing cured waste forms to moist soil and DI water in a 1-D experimental configuration. More specifically, the effect of these exposure conditions on Tc leachability as a function of distance from the exposed surface was determined.

Background

Low temperature waste forms are currently being used and considered for solidification of low-level radioactive wastes across the DOE complex. Examples include saltstone, a cementitious waste form used at the Savannah River Site (SRS) to immobilize low-activity sodium salt waste, and Cast Stone which was recently selected for solidification of secondary waste from the Hanford Tank Waste Treatment and Immobilization Plant (WTP). Cast Stone is also being considered to provide supplemental Low Activity Waste (LAW) immobilization capacity for the Hanford site.

Both the SRS and Hanford waste streams contain soluble technetium which may require stabilization to meet disposal requirements. Technetium stabilization is a difficult problem because: 1) Tc is soluble and very mobile in the oxidized form typical of near surface environments, and 2) Tc-99 is a long-lived isotope with a half-life of 2.1×10^5 years which poses a great challenge to prediction performance and places demanding requirements on the engineered barriers and environment to meet current regulatory disposal requirements.

Cast Stone and saltstone contain portland cement and fly ash in addition to ground granulated blast furnace slag (GGBFS). These hydraulic and pozzolanic ingredients react with water and other constituents in the waste stream to form the waste form matrix. The GGBFS stabilizes (reduces mobility) redox sensitive contaminants, such as, Tc and Cr. In a high pH environment, GGBFS chemically reduces

pertechnetate, Tc(VII)O_4^- , to the less soluble Tc(IV) oxidation state.¹ Over time, oxygen in the air, soil pore gas, and oxygen dissolved in the vadose zone pore water can oxidize the waste form and re-oxidize the Tc(IV) to the highly soluble Tc(VII) form.

An understanding of factors that affect the oxidation state of redox sensitive contaminants stabilized in cementitious waste forms is required to improve waste forms and engineered barriers for shallow land disposal. In addition, the parameters and relationships for the 1) rate of bulk matrix oxidation and 2) potential for and efficiency of re-reduction of soluble Tc in cured un-oxidized portions of waste forms are required for predicting long-term performance.

EXPERIMENTAL METHOD

A method for measuring contaminant oxidation fronts for redox sensitive contaminants in cementitious waste forms containing GGBFS was recently developed at the Savannah River National Laboratory (SRNL) [4, 5, and 6]. This method is based upon leaching depth-discrete subsamples obtained as a function of distance from an exposed surface. Leaching is performed in a zero head space container using deionized, de-aerated water to minimize oxidation during the leaching process. Leaching time was 48 ± 4 hours.

Waste Form Sample Preparation

Simulant. The Hanford Tank Waste Operations System (HTWOS) “Average” 5 M Na simulant was used rather than the CBP reference waste form [7] because the materials are very similar and the Tc-spiked cast stone samples were already prepared. The composition was derived from an overall average of the 1046 weeks of modeled LAW feed to a supplemental immobilization facility over a 20 year mission and is referred to as the HTWOS “Average” 5 M Na simulant [8, 9, 10]. The overall average concentrations in this simulant are listed in Table 1. The ingredients and proportions in the 5M Na simulated are provided in Table 2. Compounds were added to the liquid in the order they are listed in Table 2. Tc-99 was added to the 5 M Na simulant prior to addition of the premixed reagents as NH_4TcO_4 as indicated in Table 3.

Table 1. LAW 5 M Simulant based on Hanford Tank Waste Operations Simulator (HTWOS) modeling [9].

Waste Constituent	HTWOS Overall Average Concentration		
	(moles / L)	(g / L)	(mg / g)*
Na	5.000	115.00	93.50
K	0.03	1.28	1.04
Al	0.31	8.28	6.73
Cl	0.04	1.5	1.22
F	0.030	0.6	0.49
S	0.090	2.74	2.23
P	0.050	1.52	1.24
NO ₂	0.57	26	21.14
NO ₃	1.63	101	82.11
CO ₃	0.27	16.5	13.41
OH	1.56	26.5	21.54

* 1 ml 5 M Na simulant = 1.230g 5M simulant. 1 gram of Cast Stone made with 5 M Na simulate and a water to cementitious solids ratio = 0.60 contains 0.451g 5 M Na simulant.

¹ The fraction of pertechnetate chemically reduced to the less soluble Tc(VI) oxidation state depends on several factors including the: initial concentration, initial chemical form (inorganic or organic), and chemistry of the waste form and waste form pore solution.

Table 2. Ingredients and proportions of the 5 M Na simulant used to prepare the waste form.

Compound	Amount (g / L)
Water	819.50
Al(NO ₃) ₃ ·9 H ₂ O	115.165
50% by Weight NaOH	223.04
Na ₂ SO ₄	12.215
Na ₃ PO ₄ ·12 H ₂ O	18.5
NaCH ₃ COO·3 H ₂ O	5.25
Na ₂ CO ₃	29.05
NaNO ₃	56.79
NaNO ₂	38.975
NaCl	2.48
NaF	1.35
KNO ₃	3.33
Density	1.230
Wt.% Solids	27.06

Table 3. Tc-99 spike added to the HTWOS Average 5 M Na simulant [9].

Cast Stone w/cm	Average 5 M Na Simulant Tc-99 Concentration* (μCi / L)	Waste form Batch Size (g)	5M Na Average Simulant (g)	5M Na Average Simulant (ml)	NH ₄ TcO ₄ 0.5 mCi/ml Stock Solution (ml)	8:47:45 Cement : slag : fly ash Blend (g)	5M Waste form Tc-99 Concentration μCi / g
0.60	189	1800	812.5	660.57	0.25 (250 μL)	987.5	0.0694

* The HTWOS estimated maximum concentration for Tc-99 is 4.13 E-05 Ci / moles of Na. For 5 M Na simulant, the maximum Tc-99 value is 20.58 E-05 Ci per liter of simulant (205.8 uCi / L).

Cementitious reagents. The cement, blast furnace slag, and fly ash used in this study were obtained from a supplier in the Hanford area via PNNL and were shipped to SRNL. The three cementitious materials were pre mixed in the following proportions: portland cement : slag : fly ash ratios of 8:47:45 by mass manually shaking the bags. The cementitious materials were supplied by Hanford personnel.

Waste form. An 1800 g batch of the waste form was prepared with a water to cementitious reagent ratio (w/cm) = 0.60. See Table 4. The ingredients and proportions are shown in Table 3. The waste form slurry was mixed for 3 minutes before being transferred to 90 x 35 mm cylindrical containers. Ingredients in a 1000 g batch of cementitious waste form are shown in Table 3. The containers were filled to the top to the extent possible and capped. They were placed in an overpack container with moist towels for and cured for 103 days at ambient temperature (about 22 °C) and 65% to 75% relative humidity.

Table 4. Ingredients in Tc Spiked waste forms.

Batch Size (g)	Cement (g)	Slag (g)	Fly ash (g)	Simulant (g)
1800	79	464.1	444.4	812.5

Waste Form Exposure Conditions

Two samples, Tc2-9 and Tc2-10, were removed from the curing containers and exposed to moist Hanford sediment and DI water, respectively. Both samples were coated with 3 layers of epoxy on all sides. After the epoxy hardened which took about 3 hr., the top 2.5 cm and 2.2 cm were removed from samples Tc2-9 and Tc2-10, respectively, so that a “fresh” surface would be in contact with either DI water or as received Hanford soil. Sample Tc2-9 was placed in a container containing sieved Hanford sediment and then covered with about 3 cm of additional sediment. Sample Tc2-10 was placed in a container with DI water. Both containers had air space above the exposure media. Lids were placed on the containers and they were returned to secondary containment trays in a rad hood. See Figure 1. A summary of the curing and exposure times is provided in Table 5.



Figure 1. Epoxy coated sample with uncoated top surface, soil leaching media before sample was covered with about 3 cm of additional sediment, and container during exposure.

Table 5. Summary of curing and exposure times.

Sample	Prepared	Cured in Sealed Container (days)	Exposure Condition	Exposure Time (days)	Total Age (days)
Tc2-9	6-3-13	113	Hanford soil: 9-24-13 to 2-25-14	154	267
Tc2-10	6-3-13	113	DI water: 9-24-13 to 2-25-14	154	267

The Hanford sediment was collected in 2010 from an elevation consistent with the elevation of the sediment exposed in the Integrated Disposal Facility (IDF) [11]. The sediment was sent to SRNL by D. Wellman, PNNL, in the spring of 2013. Material from three 5-gallon buckets, Buckets 17, 18, and 19² was sieved through a No. 18 (1 mm) sieve and homogenized. The as-received moisture content of the sieved material was determined by drying at 110 °C and found to be 4.9 wt. %. (The saturated moisture content for the composite sieved sample was determined to be 9.5 wt. % based on moisture-density relationship for a maximum dry density of 134.4 lbs/cu.ft.) See Attachment 1. The material was stored in a plastic 5 gallon bucket with a lid. The sieved sediment is shown in Figure 2 (left). The coarse fraction retained on the sieve is shown in Figure 2 (right). The coarse fraction was not used in the exposure test.

² Information accompanying Buckets 17, 18, and 19 provided detailed location information C7536 I020-B24P34, C7536 I-021 B24P35, C7536 I-026 B24P40, respectively. All of the material was collected from Well: 299-E13-114: C7536: 200E.



Figure 2. Hanford sediment passing No. 18 sieve (left) and retained on No. 18 sieve (right).

Waste Form Depth Discrete Leaching

The details of the sampling and leaching methods are described elsewhere [5, 6, and 7]. In summary, layers of the waste form from 2 to over 20 mm were removed from the cylindrical monoliths starting at the top exposed surface. The wafers were size reduced in air (crushed to a powder) with a mortar and pestle. A short term leach test based on EPA 1311 was used [12]. All or a portion of the crushed wafer was weighed and placed in a leaching container. The time required for crushing, weighing and covering each sub-sample with leachate was less than 10 minutes. Deionized, de-aerated ASTM Type I/II water was used as the leachate. Zero head space leaching containers were used to minimize exposure to oxygen and sample oxidation during leaching. The filled leach vessels were loaded into a large mouth plastic bottle which was tumbled end-over-end at 30 rpm for 48 ± 2 hours.

After tumbling, leachates were filtered using 0.45 micron filters attached to 20 mL syringes. Ca, K, Al, and Na concentrations were measured using an Inductively Coupled Plasma- Optical Emission Spectrometer (ICP-OES), Varian 730-ES. NO_3^- , NO_2^- , and SO_4^{2-} were analyzed using Ion Chromatography (IC), Dionex ICS-5000 EG. Tc-99 was analyzed by liquid scintillation. Sample preparation and the appearance of the leachates before tumbling and after filtering are illustrated in earlier reports [5 and 6]. Leaching results for all analytes are tabulated in Attachment 2.

Fraction Leached. The fraction of selected anions and cations leached or percent leached (fraction leached X 100) from each crushed subsample was selected as the parameter for indicating 1) the effect of exposure to air (i.e., oxidation) on the redox sensitive contaminants such as TcO_4^- and CrO_4^{2-} , Na and NO_3^- and 2) the depth of penetration of oxygen into the waste form (i.e., rate of oxidation front advancement). The percent leached was calculated using Equation 1.

$$\text{Equation 1. } \% \text{ Leached} = 100 * \left(\frac{m_{i\text{-leachate}}}{m_{i\text{-total in solid}}} \right)$$

Where:

$m_{i\text{-leached}}$ = mass of species i leached (mg). The leachate was filtered prior to analysis using a 0.45 μm filter.

$M_{i\text{-total}}$ = mass of species i in the subsample leached (mg). The total amount in the waste form was approximated and only reflects the contribution to the waste form from the spiked mixing solution.

RESULTS

Two samples, Tc2-9 and Tc2-10 with identical curing histories were coated with epoxy and the top 25 to 22 mm were removed from the samples to achieve a “fresh” cut surfaces. See Figure 3. Sample Tc2-9 was exposed to Hanford sediment with 4.5 % moisture (as received condition). Sample Tc2-10 was exposed to DI water. After exposure for 154 days, the depth-discrete subsamples were cut, crushed and leached in deaerated, DI water in zero head space container.

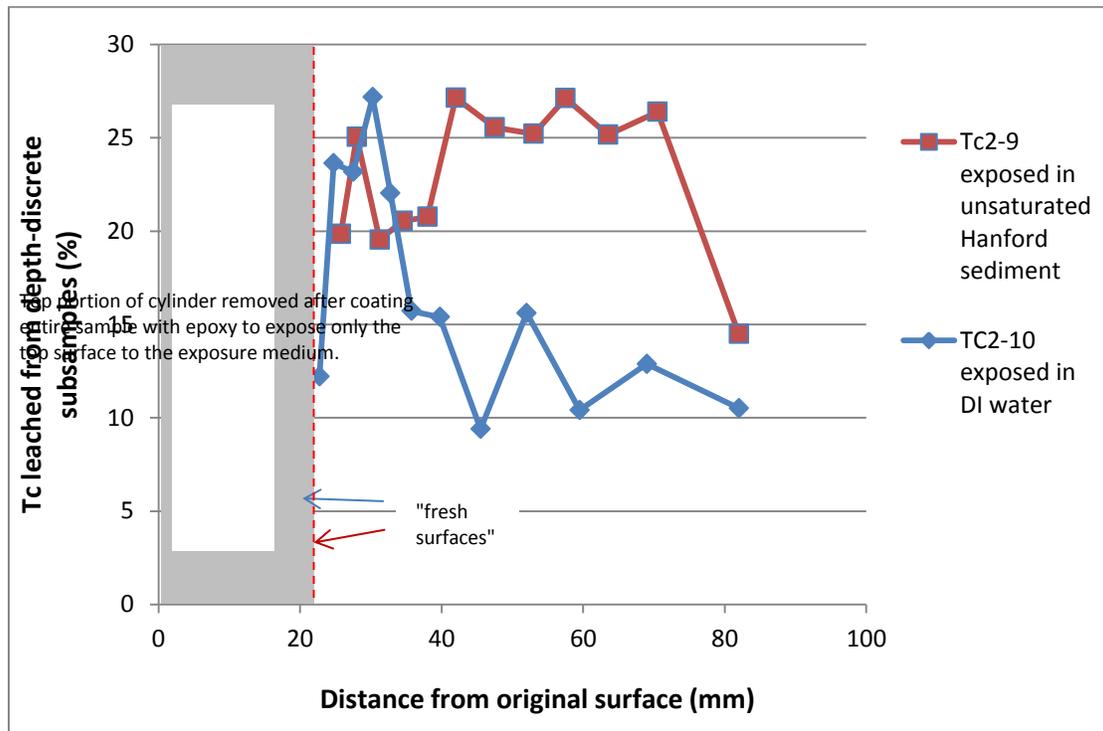


Figure 3. Percent Tc-99 leached from depth-discrete subsamples as a function of distance from the as cast sample illustrating that the top portion was removed in order to expose a “fresh” surface to unsaturated Hanford sediment and DI water.

Tc-99 Leaching

Tc-99 leachate results are provided in Tables 6 and 7, respectively. Results are re-plotted in Figure 4 as a function of the “fresh surface” sample. Subsample leaching results from the top 10 to 15 mm of the “fresh” cut surfaces of both samples showed an initial depletion and then a spike in the mass fraction Tc-99. The spike was more apparent for the sample exposed to DI water.

The Tc fraction leached from depth-discrete subsamples of Tc2-9 (exposed to Hanford sediment) dropped back to the value measured for the surface subsample between about 3 and 12 mm before increasing to 0.25 to 0.27. The mass fraction Tc-99 leached from bottom subsample (16mm thick) dropped to the lowest value measured, 0.145, and may indicate the oxidation front resulting from exposure in soil.

The Tc-99 mass fraction leached from depth-discrete subsamples of Tc2-10 (exposed to DI water) dropped to 0.09 to 0.16 between 12 and 65 mm below the exposed surface. The leveling off of the

leachable Tc below 12 mm may indicate the location of the oxidation front resulting from oxygen supplied to the fresh cut surface by the DI water.

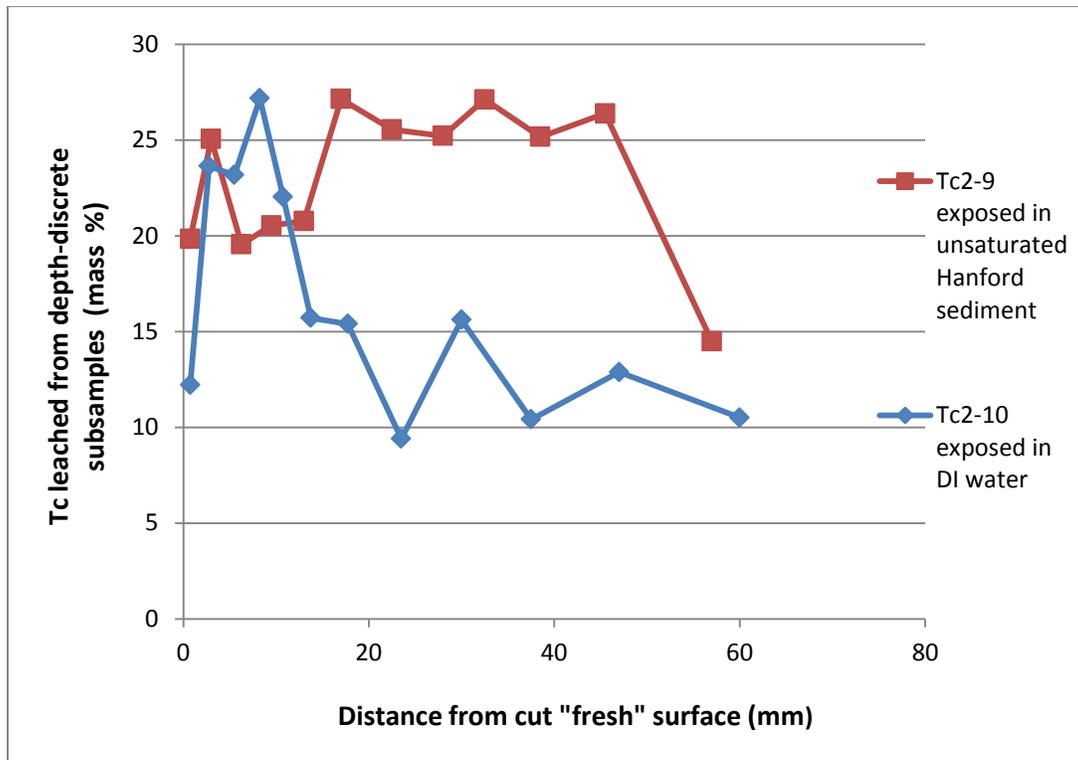


Figure 4. Percent Tc-99 leached from depth-discrete subsamples as a function of distance from fresh surfaces exposed to unsaturated Hanford sediment and DI water.

The lowest Tc-99 mass fractions leached from Tc2-9 and Tc2-10 subsamples were 0.155 and 0.094, respectively. Soluble Tc-99 throughout the entire length of these samples may be due to one or several of the following:

- Oxidation during exposure to Hanford unsaturated soil (Tc2-9) and DI water (Tc2-10).
- Oxidation during the subsampling, grinding, weighing, and leaching process. (Previous results indicate that $\leq 5\%$ of the Tc oxidized during sample handling and leaching [6]).
- Incomplete reduction of the Tc(IV) by the waste form.
- Movement of re-oxidized Tc throughout the sample during curing and exposure.
- Incomplete isolation of all surfaces of the cylindrical samples with respect to oxygen. Only the top surface was intended to be exposed to the environmental media.

Table 6. Tc-99 leachate results for depth-discrete subsample cut from Sample Tc2-9 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

Tc 2-9 waste form sub-sample No.	Sample length, distance from top surface (mm)	Ave. sub-sample thickness (mm)	Sub-sample ave. distance from top surface (mm)	Sub sample mass (g)	Leachate mass (g)	Tc leached from Tc 2-9 (dpm/ml)	Tc leached from Tc2-9 (uCi/ml)	uCi Tc/ 1g waste form	Tc leached (uCi)	Tc in sample before leached (uCi)	% Tc leached
--	65	0	--	--	--	--	--	--	--	--	--
1	63.5	1.5	0.8	2.14	41.6762	1.57E+03	7.07E-04	6.94E-02	2.95E-02	1.49E-01	19.85
2	60.5	3	3.0	2.9398	41.881	2.71E+03	1.22E-03	6.94E-02	5.11E-02	2.04E-01	25.06
3	57	3.5	6.3	3.2305	40.7152	2.39E+03	1.08E-03	6.94E-02	4.38E-02	2.24E-01	19.55
4	54	3	9.5	4.5142	39.9093	3.58E+03	1.61E-03	6.94E-02	6.44E-02	3.13E-01	20.54
5	50	4	13.0	2.6674	41.0332	2.08E+03	9.37E-04	6.94E-02	3.84E-02	1.85E-01	20.77
6	46	4	17.0	3.2903	40.5942	3.39E+03	1.53E-03	6.94E-02	6.20E-02	2.28E-01	27.15
7	39	7	22.5	3.5838	40.7836	3.46E+03	1.56E-03	6.94E-02	6.36E-02	2.49E-01	25.56
8	35	4	28.0	2.9481	41.5034	2.76E+03	1.24E-03	6.94E-02	5.16E-02	2.05E-01	25.22
9	30	5	32.5	2.5505	39.7714	2.68E+03	1.21E-03	6.94E-02	4.80E-02	1.77E-01	27.12
10	23	7	38.5	3.6458	40.6267	3.48E+03	1.57E-03	6.94E-02	6.37E-02	2.53E-01	25.17
11	16	7	45.5	3.5538	40.7068	3.55E+03	1.60E-03	6.94E-02	6.51E-02	2.47E-01	26.39
12	0	16	57.0	3.9778	40.7542	2.18E+03	9.82E-04	6.94E-02	4.00E-02	2.76E-01	14.50

Table 7. Tc-99 leachate results for depth-discrete subsample cut from Sample Tc2-10 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in DI water.

Tc 2-10 waste form sub-sample No.	Sample length, distance from top surface (mm)	Ave. sub sample thickness (mm)	Sub-sample ave. distance from top surface (mm)	Sub-sample mass (g)	Leachate mass (g)	Tc leached from Tc 2-9 (dpm/ml)	Tc leached from Tc2-9 (uCi/ml)	uCi Tc/ 1g waste form	Tc leached (uCi)	Tc in sample before leached (uCi)	% Tc leached
--	68	0	0	--	--	--	--	--	--	--	--
1	66.5	1.5	0.8	2.1023	41.2665	9.59E+02	4.32E-04	6.94E-02	1.78E-02	1.46E-01	12.22
2	64	2.5	2.8	2.6947	41.066	2.39E+03	1.08E-03	6.94E-02	4.42E-02	1.87E-01	23.64
3	61	3	5.5	3.5261	40.8766	3.08E+03	1.39E-03	6.94E-02	5.67E-02	2.45E-01	23.17
4	58.5	2.5	8.3	3.2316	40.7629	3.32E+03	1.50E-03	6.94E-02	6.10E-02	2.24E-01	27.18
5	56	2.5	10.8	3.1107	41.0904	2.57E+03	1.16E-03	6.94E-02	4.76E-02	2.16E-01	22.03
6	52.5	3.5	13.8	4.8403	39.87	2.94E+03	1.32E-03	6.94E-02	5.28E-02	3.36E-01	15.72
7	48	4.5	17.8	6.424	39.2801	3.88E+03	1.75E-03	6.94E-02	6.87E-02	4.46E-01	15.40
8	41	7	23.5	9.9767	37.3432	3.87E+03	1.74E-03	6.94E-02	6.51E-02	6.92E-01	9.40
9	35	6	30.0	6.2243	39.6078	3.78E+03	1.70E-03	6.94E-02	6.74E-02	4.32E-01	15.61
10	26	9	37.5	7.4323	38.5899	3.09E+03	1.39E-03	6.94E-02	5.37E-02	5.16E-01	10.41
11	16	10	47.0	5.7655	39.8804	2.87E+03	1.29E-03	6.94E-02	5.16E-02	4.00E-01	12.89
12	0	16	60.0	7.632	38.6221	3.20E+03	1.44E-03	6.94E-02	5.57E-02	5.30E-01	10.51

Nitrate and Sodium Leaching

Nitrate and sodium are not redox sensitive species under the curing and exposure conditions of this test. Depth-discrete subsamples leachate results for sodium and nitrate are provided in Tables 8 to 11 and are plotted in Figure 4 for comparison with technetium, a redox sensitive radionuclide. Nitrate is not bound in any low solubility solid phases. However, a portion of the sodium is thought to be bound in calcium silicate hydrate phases and calcium aluminate hydrate phases [Langton, 2014] and is therefore not completely soluble.

An initial depletion in leachable nitrate and sodium is more obvious for these species than for Tc. The NO_3^- and Na mass fractions leached from depth-discrete subsamples below about 10 to 15 mm showed a slight downward trend from about 15 mm to the final bottom subsample.

Slightly higher mass fractions of Na and NO_3^- were leached from depth-discrete subsamples of samples Tc2-9 (exposed to Hanford sediment) below about 15mm than from corresponding depth-discrete samples of Tc2-10 (cured in Hanford sediment). Somewhat higher fractions of Na were leached from the Tc2-9 (exposed to sediment) subsamples than from Tc2-10 which was exposed to DI water. The reverse was found for NO_3^- . Higher fractions of NO_3^- were leached from subsamples of Tc2-10 (exposed to DI water) when compared to subsamples of Tc2-9 (exposed to moist Hanford sediment).

The low Na and NO_3^- mass fractions leached from the near surface subsamples of Tc2-9 and Tc2-10 strongly suggests that the top portions of these samples were depleted in Na, and NO_3^- prior to the depth-discrete sampling due to migration of these soluble ions into the exposure media. Consequently the actual mass of these ions in the uppermost depth-discrete subsamples after exposure was less than the mass calculated for the original material.

Based on the mass fraction of nitrate leached (assumed to be 100 % soluble throughout the curing and exposure), the depth of depletion in Tc2-9 (exposed to Hanford sediment) was about 9.5 mm and in Tc2-10 exposed to DI water it was about 3 mm. Inhomogeneity due to settling or surface effects resulting from sample preparation is unlikely in these samples because the top 2.2 to 2.5 cm of the as cast sample was removed within a few minutes prior to exposure.

In addition, about 24 percent of the Tc-99 in the subsamples of Tc2-9 (exposed to Hanford sediment) between 0.8 and 46 mm was extracted in the depth-discrete leaching test. About 24 percent of the Tc-99 in the subsamples of Tc2-10 (exposed to DI water) was extracted between 0.8 and 11 mm. This is about 2X as much as was leached from the lower portions of both samples. These data suggest that oxidation of the reduced Tc species extended further into the sample exposed to unsaturated Hanford sediment compared to the samples exposed to DI water. A summary of the fractions Na, NO_3^- and Tc leached as a function of distance from the exposed surfaces of Tc2-9 and Tc2-10 is provided in Table 12.

Table 8. Na leachate results for depth discrete-subsample cut from Sample Tc2-9 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

Tc 2-9 waste form sub-sample no.	Ave. distance from top surface (mm)	Sub-sample mass (g)	Leachate mass (g or ml)	Na leached from Tc 2-9 (mg/L)	mg Na in 1g waste form	Na Leached (mg)	Na in sample before leached (mg)	% Na leached
1	0.8	2.14	41.6762	898	42.07	37.43	90.03	41.57
2	3	2.9398	41.881	1750	42.07	73.29	123.68	59.26
3	6.3	3.2305	40.7152	2630	42.07	107.08	135.91	78.79
4	9.5	4.5142	39.9093	2600	42.07	103.76	189.91	54.64
5	13	2.6674	41.0332	2550	42.07	104.63	112.22	93.24
6	17	3.2903	40.5942	3160	42.07	128.28	138.42	92.67
7	22.5	3.5838	40.7836	3380	42.07	137.85	150.77	91.43
8	28	2.9481	41.5034	2830	42.07	117.45	124.03	94.70
9	32.5	2.5505	39.7714	2380	42.07	94.66	107.30	88.22
10	38.5	3.6458	40.6267	3170	42.07	128.79	153.38	83.97
11	45.5	3.5538	40.7068	3270	42.07	133.11	149.51	89.03
12	57	3.9778	40.7542	3110	42.07	126.75	167.35	75.74

Table 9. NO₃⁻ leachate results for depth discrete-subsample cut from Sample Tc2-9 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in DI water.

Tc 2-9 waste form sub-sample no.	Ave. distance from top surface (mm)	Sub-sample mass (g)	Leachate mass (g or ml)	NO ₃ ⁻ leached from Tc 2 -9 (mg/L)	mg NO ₃ ⁻ in 1g waste form	NO ₃ ⁻ Leached (mg)	NO ₃ ⁻ in sample before leached (mg)	% NO ₃ ⁻ Leached
1	0.8	2.14	41.6762	583	36.3	24.30	77.66	31.29
2	3	2.9398	41.881	1567	36.3	65.63	106.69	61.52
3	6.3	3.2305	40.7152	2597	36.3	105.74	117.23	90.19
4	9.5	4.5142	39.9093	2243	36.3	89.52	163.82	54.64
5	13	2.6674	41.0332	2420	36.3	99.30	96.80	102.58
6	17	3.2903	40.5942	3005	36.3	121.99	119.40	102.16
7	22.5	3.5838	40.7836	3165	36.3	129.08	130.06	99.25
8	28	2.9481	41.5034	2668	36.3	110.73	106.99	103.50
9	32.5	2.5505	39.7714	2239	36.3	89.05	92.56	96.21
10	38.5	3.6458	40.6267	3014	36.3	122.45	132.31	92.55
11	45.5	3.5538	40.7068	3048	36.3	124.07	128.97	96.21
12	57	3.9778	40.7542	3042	36.3	123.97	144.35	85.88

Table 10. Na leachate results for depth-discrete subsample cut from Sample Tc2-10 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

Tc 2-10 wasteform sub-sample no.	Ave. distance from top surface (mm)	Sub-sample mass (g)	Leachate mass (g or ml)	Na leached from Tc 2-10 (mg/L)	mg Na in 1g waste form	Na leached (mg)	Na in sample before leached (mg)	% Na leached
1	0.8	2.1023	41.2665	515	42.07	21.25	88.44	24.03
2	2.8	2.6947	41.066	1450	42.07	59.55	113.37	52.53
3	5.5	3.5261	40.8766	2820	42.07	115.27	148.34	77.71
4	8.3	3.2316	40.7629	2750	42.07	112.10	135.95	82.45
5	10.8	3.1107	41.0904	2930	42.07	120.39	130.87	92.00
6	13.8	4.8403	39.87	4380	42.07	174.63	203.63	85.76
7	17.8	6.424	39.2801	5720	42.07	224.68	270.26	83.14
8	23.5	9.9767	37.3432	8070	42.07	301.36	419.72	71.80
9	30.0	6.2243	39.6078	5540	42.07	219.43	261.86	83.80
10	37.5	7.4323	38.5899	6270	42.07	241.96	312.68	77.38
11	47.0	5.7655	39.8804	4880	42.07	194.62	242.55	80.24
12	60.0	7.632	38.6221	5840	42.07	225.55	321.08	70.25

Table 11. NO₃⁻ leachate results for depth-discrete subsample cut from Sample Tc2-10 cured in a humid environment after which a ‘freshly cut’ surface was exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

Tc 2-10 wasteform sub-sample no.	Ave. distance from top surface (mm)	Sub-sample mass (g)	Leachate mass (g or ml)	NO₃⁻ Leached from Tc 2-10 (mg/L)	mg NO₃⁻ in 1g ss	NO₃⁻ Leached (mg)	NO₃⁻ in sample before leached (mg)	% NO₃⁻ Leached
1	0.8	2.1023	41.2665	153	36.3	6.31	76.29	8.28
2	2.8	2.6947	41.066	1120	36.3	45.99	97.79	47.03
3	5.5	3.5261	40.8766	2780	36.3	113.64	127.96	88.81
4	8.3	3.2316	40.7629	2710	36.3	110.47	117.27	94.20
5	10.8	3.1107	41.0904	2950	36.3	121.22	112.89	107.38
6	13.8	4.8403	39.87	4360	36.3	173.83	175.65	98.96
7	17.8	6.424	39.2801	6060	36.3	238.04	233.13	102.11
8	23.5	9.9767	37.3432	9320	36.3	348.04	362.05	96.13
9	30.0	6.2243	39.6078	5740	36.3	227.35	225.88	100.65
10	37.5	7.4323	38.5899	6900	36.3	266.27	269.72	98.72
11	47.0	5.7655	39.8804	5170	36.3	206.18	209.23	98.54
12	60.0	7.632	38.6221	6530	36.3	252.20	276.97	91.06

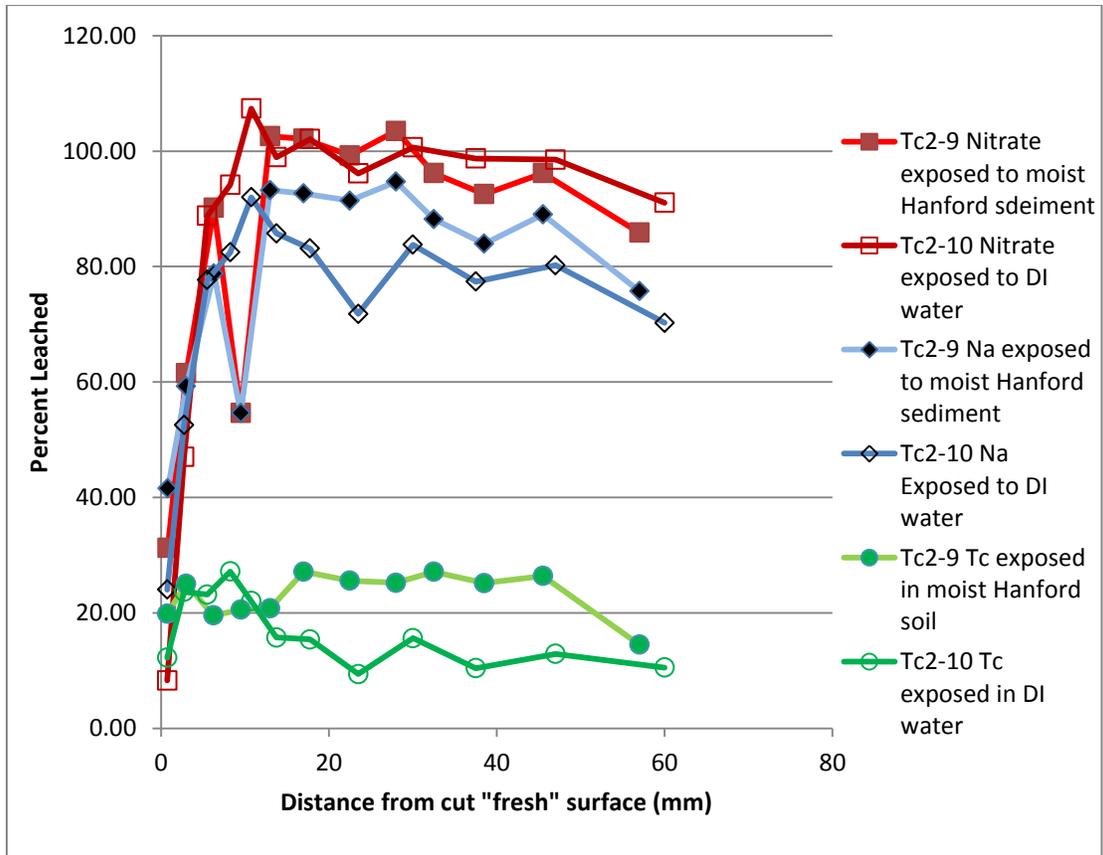


Figure 5. Na, NO₃⁻, and Tc-99 percents leached from depth-discrete subsamples as a function of distance from fresh surfaces exposed to unsaturated Hanford sediment and DI water.

Table 12. Summary of NO₃⁻, Na, and Tc leached as a function of distance from top surface of TC2-9 (exposed to Hanford sediment) and Tc2-10 (exposed to DI water).

Tc2-9 Exposed to Hanford sediment				Tc2-10 Exposed to DI water			
Distance from exposed surface (mm)	NO ₃ ⁻	Na	Tc	Distance from exposed surface (mm)	NO ₃ ⁻	Na	Tc
	% Leached				% Leached		
0 to 0.8	31	42	20	0 to 0.8	8	24	12
0.8 to 9.5	69	64	24	0.8 to 3	47	53	24
9.5 to 46*	99	91		3 to 60	97	80	--
46 to 57	86	76	13	3 to 11*	--	--	24
--	--	--	--	11 to 60	--	--	13

* Approximate depth of oxygen ingress during exposure.

Red shading in Table 12 indicates the subsample depths relative to fresh cut surfaces from which soluble ions were removed as the result of migration into the leaching media. Consequently, less than 100 % of the original soluble ion concentrations were present in the samples at the time depth-discrete subsamples were prepared and leached. See Equation 2.

Equation 2.
$$\frac{\text{Mass extracted from depth-discrete subsample}}{\text{(Initial concentration - Mass transferred to soil / water)}}$$

CONCLUSIONS

Based on the results presented in this report, leaching crushed depth-discrete subsamples appears to be a suitable method for evaluating the effects of exposure to moist air and other environmental conditions expected in disposal environments on solubility / leachability of redox sensitive contaminants in cementitious waste forms. The method is useful in identifying the contaminant specific oxidation fronts in cured chemically reducing cementitious waste forms and provides the mass fraction of soluble redox sensitive contaminants and other soluble contaminants as a function of distance from a surface exposed to moist air. The soluble fraction of a chemical species is that portion available to diffusion through the waste form pore solution. The effective diffusion coefficients for the soluble fractions of redox sensitive contaminants will be approximately the same as that for nitrate.

Coating all sides of a cylindrical sample with an impermeable epoxy and cutting a fresh surface 2 to 2.5 cm from the original top surface eliminates potential sample inhomogeneity as the result of settling as a reason from observed results and provides 1-D soluble ion transport and gas transport information.

Based on nitrate (assumed to 100 % soluble during curing and exposure) leaching results for the depth-discrete subsamples depletion regions were identified which extended 9.5 and 3 mm into samples Tc2-9 (exposed to Hanford sediment) and Tc2-10 (DI water). Lower mass fractions of nitrate were leached from the depth-discrete samples taken from these near surface locations presumably because a significant portion of the nitrate had already migrated into the soil or water. Subsample leaching results can be interpreted in the same way for the same regions in the two samples tested.

Soluble Tc was leached from all of the depth-discrete subsamples from both Tc2-9 and Tc2-10 which strongly suggests that oxygen was present in the entire length of both samples. About 24 mass percent of the Tc in the original sample, was leached (soluble) from subsamples between 0.8 and 46 mm below the exposed surface of Tc2-9 (exposed to Hanford sediment). The same percent (24%) was leached from the subsamples between 0.8 and 11 mm below the exposed surface of Tc2-10 (exposed to DI water). This suggests that the rate of oxygen migration into the sample exposed to soil was faster than the rate of migration into the sample exposed to water which is consistent with the more rapid transport of ions through a gas phase as compared to a liquid phase. It is assumed that moisture in the Hanford sediment was not sufficient to completely block the surface pores with respect to gas transport across the soil-waste form boundary.

Additional data are required to fully understand and quantify the progression of the region depleted in soluble ions and the rate of oxygen ingress and oxidation of redox sensitive contaminants such as Tc. However, these scoping studies provide insights of the multiple mechanisms affecting the solubility and leachability of redox sensitive contaminants.


In conclusion, leaching monolithic porous cementitious waste forms in water appears to be non-conservative for determining the concentration of soluble redox sensitive contaminants such as TcO_4^- and CrO_4^{2-} in a waste form. Under saturated conditions (leaching in water) the water blocks the pores and inhibits oxygen transport due to the low solubility of oxygen in water. However, under drying conditions or partially saturated conditions, oxygen can diffuse through the gas phase at a rate several orders of magnitude higher than diffusion through water. Once oxidized the redox sensitive contaminants are soluble and available to be leached via diffusion and / or advection.

Leaching monolithic samples in water provides effective diffusion coefficients which takes into account porosity, tortuosity, i.e., physical entrapment, of soluble species. Leaching crushed samples provides a means of estimating the concentrations of soluble contaminants in a waste form.

REFERENCES

1. Shuh, D. K., N. Kaltsoyannis, J. J. Bucher, N. M. Edelstein, S. B. Clark, H. Nitsche, W. Lukens, W. S. Yang, and J. C. Bryan, 1994. "Environmental Applications of XANES: Speciation of Tc in Cement after Chemical Treatment with Se after Bacterial Uptake," *Mat. Res. Soc. Symp. Proc. #44*, P. 323-3328.
2. Shuh, D. K., N. M. Edelstein, C. J. Burns, W. W. Lukens, 2003. Research Program to Investigate the Fundamental Chemistry of Technetium, EMSP-73778, Lawrence Berkeley National Laboratory, Berkeley, CA.
3. Lukens, W. W., J. J. Bucher, D. K. Shuh, and N. M. Edelstein, 2005. "Evolution of Technetium Speciation in Reducing Grout," *Environ. Sci. Technol.* 30:8064-8070.
4. Almond, P. M. and C. A. Langton, 2013. "Task Technical and Quality Assurance Plan for Characterization of the Technetium Oxidation Front for Cast Stone," SRNL-RP-2013-00112, Savannah River National Laboratory, Aiken, SC 29808.
5. Almond, P. M., D. I. Kaplan, C. A. Langton, D. B. Stefanko, W. A. Spencer, A. Hatfield, and Y. Arai. 2012. "Method Evaluation and Field Sample Measurements for the Rate of Movement of the Oxidation Front in Saltstone," SRNL-STI-2012-00468, Revision 0, Savannah River National Laboratory, Savannah River Site, Aiken, SC, 29808.
6. Langton, C. A., D. B. Stefanko, and H. H. Burns, 2012. "Saltstone Oxidation Study: Leaching Method," SRNL-STI-2012-00728, Savannah River National Laboratory, Savannah River Site, Aiken, SC, 29801 and WM Symp., Feb. 24 to 28, 2013, Phoenix AZ.
7. Langton, C. A. Langton, D. S. Kosson, A. C. Garrabrants, K. G. Brown, 2009. "Reference Cases for Use in the Cementitious Barriers Partnership Project" WM Symp., March 1-5, 2009, Phoenix AZ.
8. US DOE Inter-Entity Work Order, EWO No. MOSRV00091, 2013. "Low Temperature Waste Forms Coupled with Tc Removal / Waste Feed Acceptance and Product Qualification.
9. Certa, P. J., P.A. Empey, and N. M. Wells, 2011. "River Protection Project System Plan," ORP-11242, Revision 6, Washington River Protection Solutions, LLC, Richland Washington.
10. Russell, R. L., A. D. Cozzi, et. al., 2013. "Letter Report: LAW Simulant Development for Cast Stone Screening Tests," PNNL-22352, Pacific Northwest National Laboratory, Richland, WA.
11. Wellman, D., 2013. Personal communication between D. Wellman, Pacific Northwest national Laboratory, WA and C. A. Langton, Savannah River National Laboratory, SC.
12. U.S. EPA, (2007). "Toxicity Characteristic Leaching Procedure, Method 1311," U.S. Environmental Protection Agency, SW 846, Rev. 6, Feb. 2007, Washington DC.
13. ASTM D 2216 2010. "Standard Test Methods for Laboratory Determination of Water (Moisture) Content of Soil and Rock by Mass," American Society of Testing and Materials, Philadelphia, PA.

**ATTACHMENT 1. CHARACTERIZATION OF AS-RECEIVED HANFORD
SOIL MOISTURE CONTENT AND SATURATED MOISTURE CONTENT [13]**

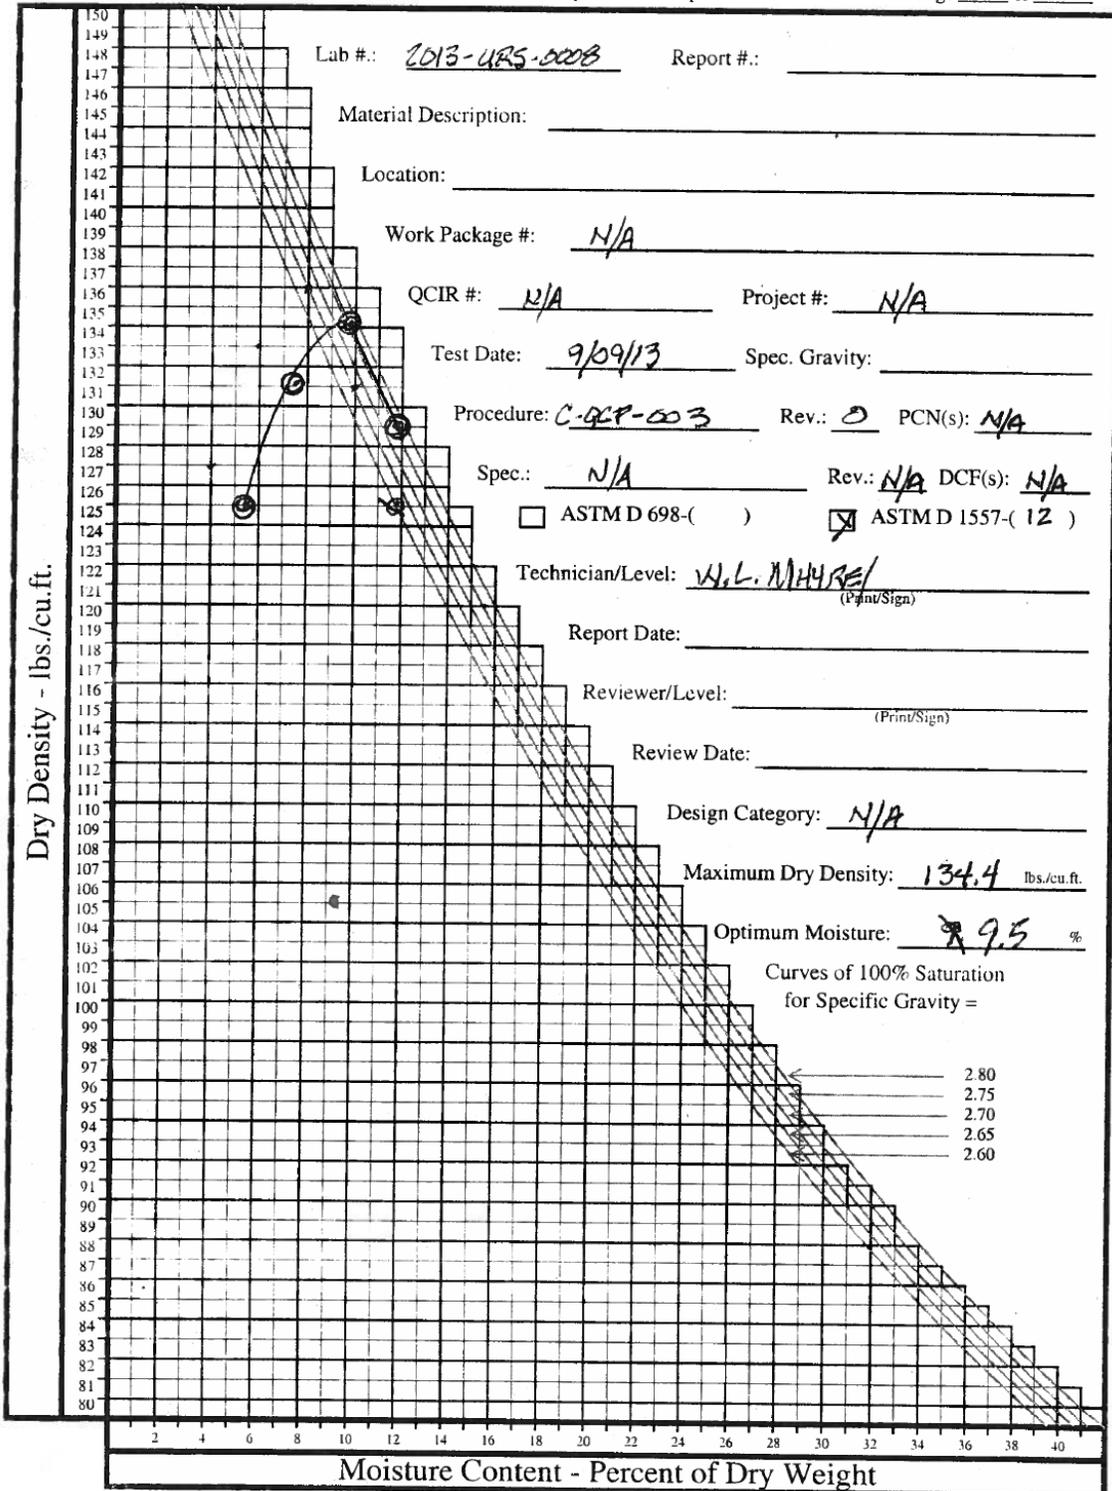

THIS REPORT SHALL NOT BE REPRODUCED, EXCEPT IN FULL, WITHOUT THE WRITTEN APPROVAL OF THE LABORATORY.

Savannah River Site

Determination of Water Content

ASTM D 2216-() Oven-Dry ASTM D 4643-() Microwave

Report No.: _____ Work Package No.: _____
 Project No.: _____ QCIR No.: _____
 Lab. No.: 2013-URS-0051 Date Tested: 8/20/13 Acceptance Criteria: NA
 Material Description: 02016 HANFORD
 Location: HANFORD SAMPLES

Test Number	18	19				
Elev. / Depth	N/A	N/A				
Sample No./Microwave No.	18-P23	19-MR4				
A. Weight of Wet Sample + Tare	259.1g	263.9g				
B. Weight of Dry Sample + Tare	246.9g	251.5g				
C. Weight of Moisture (A - B)	12.2	12.4				
D. Tare Weight	N/A	N/A				
E. Weight of Dry Sample (B - D)	246.9	251.5				
F. Percent Moisture (C / E x 100)	4.9	4.9				
Test Number						
Elev. / Depth						
Sample No./Microwave No.						
A. Weight of Wet Sample + Tare						
B. Weight of Dry Sample + Tare						
C. Weight of Moisture (A - B)						
D. Tare Weight						
E. Weight of Dry Sample (B - D)						
F. Percent Moisture (C / E x 100)						

Minimum Size Sample: Conforming Nonconforming Remarks: _____
 More Than One Soil Type: _____
 Drying Method: 230 +/- 9 Deg. F Other: _____ Microwave Time Setting: _____
 Material (Size/Amount) Excluded From Test: _____

M&TE:	Cal. Due Date:	Procedure:
		Rev.:
NCR No.:		PCN(s):
Test Results: <input type="checkbox"/> Conforming <input type="checkbox"/> Nonconforming <input type="checkbox"/> N/A		Spec.:
Remarks:		Rev.:
		DCF(s):
		Design Category:
Technician (Print/Sign): _____	Level: _____	Date: _____
Reviewer (Print/Sign): _____	Level: _____	Date: _____

THIS REPORT SHALL NOT BE REPRODUCED, EXCEPT IN FULL, WITHOUT THE WRITTEN APPROVAL OF THE LABORATORY.

ATTACHMENT 2. ANALYTICAL RESULTS FOR SUBSAMPLE LEACHATES

Table 13. Cation and anion leachate results for depth discrete subsample cut from Sample Tc2-9 cured at ambient temperature in a humid environment. The “fresh” top surface was subsequently exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

3/13/2014 12:41	Sample	Ag	Al	B	Ba	Be	Ca	Cd	Ce	Co	Cr	Cu	Fe
ADS No.	No.	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
300309532	TC 2_9_1	< 0.1	24	2.34	< 0.1	< 0.01	2.89	< 0.1	< 1.1	< 0.2	< 0.2	< 0.3	< 0.3
300309533	TC 2_9_2	< 0.135	44.1	3.04	< 0.07	< 0.01	18.2	< 0.14	< 1.13	< 0.239	< 0.163	<	0.439
300309534	TC 2_9_3	< 0.135	42.9	3.4	< 0.07	< 0.01	22.8	< 0.14	< 1.13	< 0.239	< 0.239	<	0.79
300309535	TC 2_9_4	< 0.135	47.7	3.37	< 0.07	< 0.01	23.2	< 0.14	< 1.13	< 0.239	< 0.163	<	< 0.572
300309536	TC 2_9_5	< 0.135	45.9	3.27	< 0.07	< 0.01	20.2	< 0.14	< 1.13	< 0.239	< 0.163	<	1.72
300309537	TC 2_9_6	< 0.135	52.6	3.92	< 0.07	< 0.01	18.3	< 0.14	< 1.13	< 0.239	< 0.163	<	1.04
300309538	TC 2_9_7	< 0.135	54.5	4.09	< 0.07	< 0.01	17.6	< 0.14	< 1.13	< 0.239	< 0.163	<	0.816
300309539	TC 2_9_8	< 0.135	47.3	3.53	< 0.07	< 0.01	19.2	< 0.14	< 1.13	< 0.239	< 0.163	<	0.742
300309540	TC 2_9_9	< 0.135	44.7	3.07	< 0.07	< 0.01	22.8	< 0.14	< 1.13	< 0.239	< 0.163	<	1.4
300309541	TC 2_9_10	< 0.135	50.4	3.95	< 0.07	< 0.01	19.1	< 0.14	< 1.13	< 0.239	< 0.163	<	1.18
300309542	TC 2_9_11	< 0.135	50.3	3.95	< 0.07	< 0.01	19.2	< 0.14	< 1.13	< 0.239	< 0.163	<	1.37
300309543	TC 2_9_12	< 0.135	54.9	4.03	< 0.07	< 0.01	20.6	< 0.14	< 1.13	< 0.239	< 0.163	<	1.4
Relative Standard Deviation		(N/A % RSD)	(10 % RSD)	(10 % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)	(N/A % RSD)	(10-11 % RSD)				

Table 13 (continued). Cation and anion leachate results for depth-discrete subsample cut from Sample Tc2-9 cured at ambient temperature in a humid environment. The “fresh” top surface was subsequently exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

3/13/2014 12:41	Sample	Gd	K	La	Li	Mg	Mn	Mo	Na	Ni
ADS No.	No.	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
300309532	TC 2_9_1	< 0.6	26.8 (16.3 %RSD)	< 0.1	< 0.6 (N/A %RSD)	0.024 (10.1 %RSD)	< 0.1	< 1.5	898 (18.2 %RSD)	< 1.2
300309533	TC 2_9_2	< 0.572	73.8 (10.1 %RSD)	< 0.142	0.755 (159 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	1750 (15 %RSD)	< 1.2
300309534	TC 2_9_3	< 0.572	141 (10.4 %RSD)	< 0.142	0.877 (30.7 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	2630 (13.8 %RSD)	< 1.2
300309535	TC 2_9_4	< 0.572	< 0.142 (N/A %RSD)	< 0.142	< 0.01 (N/A %RSD)	< 0.091 (N/A %RSD)	< 1.49	< 1.49	2600 (12.9 %RSD)	< 1.2
300309536	TC 2_9_5	< 0.572	149 (10.3 %RSD)	< 0.142	0.542 (17.1 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	2550 (10.5 %RSD)	< 1.2
300309537	TC 2_9_6	< 0.572	187 (10.1 %RSD)	< 0.142	0.757 (19.6 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	3160 (10.3 %RSD)	< 1.2
300309538	TC 2_9_7	< 0.572	199 (10.1 %RSD)	< 0.142	0.858 (52.7 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	3380 (11.4 %RSD)	< 1.2
300309539	TC 2_9_8	< 0.572	166 (10.3 %RSD)	< 0.142	0.655 (50.7 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	2830 (10.2 %RSD)	< 1.2
300309540	TC 2_9_9	< 0.572	137 (10.1 %RSD)	< 0.142	0.838 (25.6 %RSD)	0.011 (10.1 %RSD)	< 0.091	< 1.49	2380 (12 %RSD)	< 1.2
300309541	TC 2_9_10	< 0.572	187 (10.2 %RSD)	< 0.142	0.969 (39.6 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	3170 (11.4 %RSD)	< 1.2
300309542	TC 2_9_11	< 0.572	187 (10.2 %RSD)	< 0.142	0.708 (13.9 %RSD)	< 0.01 (N/A %RSD)	< 0.091	< 1.49	3270 (10.2 %RSD)	< 1.2
300309543	TC 2_9_12	< 0.572	177 (10.1 %RSD)	< 0.142	0.766 (28.3 %RSD)	0.011 (10 %RSD)	< 0.091	< 1.49	3110 (10.9 %RSD)	< 1.2
Relative Standard Deviation		(N/A % RSD)	--	(N/A % RSD)	--	--	(N/A % RSD)	(N/A % RSD)	--	(N/A % RSD)

Table 13 (continued). Cation and anion leachate results for depth-discrete subsample cut from Sample Tc2-9 cured at ambient temperature in a humid environment. The “fresh” top surface was subsequently exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

3/13/2014 12:41	Sample	P	Pb	S	Sb	Si	Sn	Sr	Th	Ti	U
ADS No.	No.	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
300309532	TC 2 9 1	< 7.8	< 15	< 150 (N/A %RSD)	< 2.9	37.1	< 10	0.016 (10 %RSD)	< 1.2	< 0.4	< 9.7
300309533	TC 2 9 2	< 7.8	< 14.7	308 (10 %RSD)	< 2.9	17.1	< 10	0.202 (10.2 %RSD)	< 1.2	< 0.42	< 9.7
300309534	TC 2 9 3	< 7.8	< 14.7	460 (10 %RSD)	< 2.9	11.8	< 10	0.376 (14.7 %RSD)	< 1.2	< 0.42	< 9.7
300309535	TC 2 9 4	< 7.8	< 14.7	446 (10.1 %RSD)	< 2.9	14.9	< 10	0.338 (18.8 %RSD)	< 1.2	< 0.42	< 9.7
300309536	TC 2 9 5	< 7.8	< 14.7	423 (10 %RSD)	< 2.9	13.4	< 10	0.32 (12.1 %RSD)	< 1.2	< 0.42	< 9.7
300309537	TC 2 9 6	< 7.8	< 14.7	540 (10 %RSD)	< 2.9	14.2	< 10	0.346 (39.7 %RSD)	< 1.2	< 0.42	< 9.7
300309538	TC 2 9 7	< 7.8	< 14.7	563 (10.2 %RSD)	< 2.9	13.7	< 10	0.353 (45.7 %RSD)	< 1.2	< 0.42	< 9.7
300309539	TC 2 9 8	< 7.8	< 14.7	477 (10.1 %RSD)	< 2.9	14.2	< 10	0.341 (18 %RSD)	< 1.2	< 0.42	< 9.7
300309540	TC 2 9 9	< 7.8	< 14.7	395 (10.1 %RSD)	< 2.9	14.4	< 10	0.331 (12.5 %RSD)	< 1.2	< 0.42	< 9.7
300309541	TC 2 9 10	< 7.8	< 14.7	539 (10 %RSD)	< 2.9	14.5	< 10	0.358 (118 %RSD)	< 1.2	< 0.42	< 9.7
300309542	TC 2 9 11	< 7.8	< 14.7	547 (10 %RSD)	< 2.9	14.1	< 10	0.369 (12.1 %RSD)	< 1.2	< 0.42	< 9.7
300309543	TC 2 9 12	< 7.8	< 14.7	531 (10.1 %RSD)	< 2.9	14.6	< 10	0.326 (10.5 %RSD)	< 1.2	< 0.42	< 9.7
Relative Standard Deviation		(N/A % RSD)	(N/A % RSD)	--	(N/A % RSD)	(10 % RSD)	(N/A % RSD)	--	(N/A % RSD)	(N/A % RSD)	(N/A % RSD)

Table 13 (continued). Cation and anion leachate results for depth-discrete subsample cut from Sample Tc2-9 cured at ambient temperature in a humid environment. The “fresh” top surface was subsequently exposed to and leached in unsaturated Hanford sediment with 5 wt.% moisture.

3/13/2014 12:41	Sample	V	Zn	Zr	Bromide	Chloride	Fluoride	Formate	Nitrate	Nitrite	Oxalate	Phosphate	Sulfate
ADS No.	No.	mg/L	mg/L	mg/L	µG/mL	µG/mL	µG/ML	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL
300309532	TC 2 9 1	< 10	< 0.2	< 2.2	<20	12	<20	<20	583	149	<10	<10	315
300309533	TC 2 9 2	< 10.1	< 0.198	< 2.19	<20	31	<20	<20	1567	375	<10	<10	719
300309534	TC 2 9 3	< 10.1	< 0.198	< 2.19	<20	40	<20	<20	2597	637	<10	<10	1026
300309535	TC 2 9 4	< 10.1	< 0.198	< 2.19	<20	36	<20	<20	2243	544	<10	<10	905
300309536	TC 2 9 5	< 10.1	< 0.198	< 2.19	<20	36	<20	<20	2420	600	<10	<10	962
300309537	TC 2 9 6	< 10.1	< 0.198	< 2.19	<20	45	<20	<20	3005	753	<10	<10	1202
300309538	TC 2 9 7	< 10.1	< 0.198	< 2.19	<20	48	<20	<20	3165	795	<10	<10	1263
300309539	TC 2 9 8	< 10.1	< 0.198	< 2.19	<20	41	<20	<20	2668	660	<10	<10	1062
300309540	TC 2 9 9	< 10.1	< 0.198	< 2.19	<20	35	<20	<20	2239	555	<10	<10	889
300309541	TC 2 9 10	< 10.1	< 0.198	< 2.19	<20	46	<20	<20	3014	754	<10	<10	1199
300309542	TC 2 9 11	< 10.1	< 0.198	< 2.19	<20	46	<20	<20	3048	761	<10	<10	1213
300309543	TC 2 9 12	< 10.1	< 0.198	< 2.19	<20	41	<20	<20	3042	747	<10	<10	1188
Relative Standard Deviation		(N/A % RSD)	(N/A % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)	(10 % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)

Table 14. Cation and anion leachate results for depth discrete subsample cut from Sample Tc2-10 cured at ambient temperature in a humid environment. A “fresh” surface was subsequently exposed to and leached in DI water.

3/13/2014 12:41	Sample	Ag	Al	B	Ba	Be	Ca	Cd	Ce	Co	Cr	Cu	Fe
ADS No.	No.	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
300309520	TC 2_10_1	< 0.1	18.5	0.983	< 0.1	< 0.01	21.7	< 0.1	< 1.1	< 0.2	< 0.2	< 0.3	< 0.3 (N/A % RSD)
300309521	TC 2_10_2	< 0.135	35.5	2.31	< 0.07	< 0.01	34.4	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	0.78 (10.1 % RSD)
300309522	TC 2_10_3	< 0.135	47.6	3.56	< 0.07	< 0.01	27.8	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	2.17 (10.1 % RSD)
300309523	TC 2_10_4	< 0.135	48.6	3.41	< 0.07	< 0.01	27	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	0.611 (10.8 % RSD)
300309524	TC 2_10_5	< 0.135	50.7	3.65	< 0.07	< 0.01	23.2	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	2.23 (10.2 % RSD)
300309525	TC 2_10_6	< 0.135	64.9	5.22	< 0.07	< 0.01	21.1	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	7.52 (10 % RSD)
300309526	TC 2_10_7	< 0.135	74.1	6.59	< 0.07	< 0.01	13.8	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	2.96 (10 %RSD)
300309527	TC 2_10_8	< 0.135	87.1	8.21	< 0.07	< 0.01	11.4	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	3.12 (10 % RSD)
300309528	TC 2_10_9	< 0.135	69.2	6.39	< 0.07	< 0.01	11.6	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	1.69 (10.1 % RSD)
300309529	TC 2_10_10	< 0.135	75.6	6.77	< 0.07	< 0.01	13.9	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	2.13 (10.1 % RSD)
300309530	TC 2_10_11	< 0.135	64.9	5.47	< 0.07	< 0.01	16.6	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	2.66 (10.1 % RSD)
300309531	TC 2_10_12	< 0.135	70.1	6.94	< 0.07	< 0.01	16.4	< 0.14	< 1.13	< 0.239	< 0.163	< 0.275	3.46 (10.1 %RSD)
Relative Standard Deviation		(N/A % RSD)	(10 % RSD)	(10 % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)	(N/A % RSD)	--				

Table14 (continued) Cation and anion leachate results for depth-discrete subsample cut from Sample Tc2-10 cured at ambient temperature in a humid environment. A “fresh” surface was subsequently exposed to and leached in DI water.

3/13/2014 12:41	Sample	Gd	K	La	Li	Mg	Mn	Mo	Na	Ni
ADS No.	No.	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
300309520	TC 2_10_1	< 0.6	26.8 (11.3 %RSD)	< 0.1	0.739 (26.5 %RSD)	< 1	< 0.1	< 1.5	515	< 1.2
300309521	TC 2_10_2	< 0.572	59.7	< 0.142	< 0.635	< 0.964	< 0.091	< 0.091	< 1.49	< 1.2
300309522	TC 2_10_3	< 0.572	141 (10.1 %RSD)	< 0.142	0.41 (17.7 %RSD)	< 0.964	< 0.091	< 1.49	2820	< 1.2
300309523	TC 2_10_4	< 0.572	147 (10 %RSD)	< 0.142	0.941 (24.3 %RSD)	< 0.964	< 0.091	< 1.49	2750	< 1.2
300309524	TC 2_10_5	< 0.572	163 (10 %RSD)	< 0.142	0.849 (27.4 %RSD)	< 0.964	< 0.091	< 1.49	2930	< 1.2
300309525	TC 2_10_6	< 0.572	254 (10 %RSD)	< 0.142	0.978 (14 %RSD)	< 0.964	< 0.091	< 1.49	4380	< 1.2
300309526	TC 2_10_7	< 0.572	349 (10 %RSD)	< 0.142	< 0.635 (N/A %RSD)	< 0.964	< 0.091	< 1.49	5720	< 1.2
300309527	TC 2_10_8	< 0.572	507 (10 %RSD)	< 0.142	0.622 (58.6 %RSD)	< 0.964	< 0.091	< 1.49	8070	< 1.2
300309528	TC 2_10_9	< 0.572	329 (10 %RSD)	< 0.142	0.623 (42.7 %RSD)	< 0.964	< 0.091	< 1.49	5540	< 1.2
300309529	TC 2_10_10	< 0.572	385 (10 %RSD)	< 0.142	0.954 (13.9 %RSD)	< 0.964	< 0.091	< 1.49	6270	< 1.2
300309530	TC 2_10_11	< 0.572	289 (10 %RSD)	< 0.142	1.15 (41.2 %RSD)	< 0.964	< 0.091	< 1.49	4880	< 1.2
300309531	TC 2_10_12	< 0.572	344 (10 %RSD)	< 0.142	0.443 (36.6 %RSD)	< 0.964	< 0.091	< 1.49	5840	< 1.2
Relative Standard Deviation		(N/A % RSD)	(N/A % RSD)	(N/A % RSD)	--	(N/A % RSD)	(N/A % RSD)	(N/A % RSD)	(10 -11 % RSD)	(N/A % RSD)

Table 14 (continued). Cation and anion leachate results for depth-discrete subsample cut from Sample Tc2-10 cured at ambient temperature in a humid environment. A “fresh” surface was subsequently exposed to and leached in DI water.

3/13/2014 12:41	Sample	P	Pb	S	Sb	Si	Sn	Sr	Th	Ti	U
ADS No.	No.	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L	mg/L
300309520	TC 2 10 1	< 7.8	< 15	< 150	< 10	16.1	< 10	0.217	< 10	< 0.4	< 9.7
300309521	TC 2 10 2	< 7.78	< 14.7	264	< 10.1	9.08	< 10.1	0.422	< 10.1	< 0.42	< 9.74
300309522	TC 2 10 3	< 7.8	< 14.7	527	< 10.1	13.2	< 10.1	0.4	< 10.1	< 0.42	< 9.74
300309523	TC 2 10 4	< 7.8	< 14.7	520	< 10.1	13.2	< 10.1	0.375	< 10.1	< 0.42	< 9.74
300309524	TC 2 10 5	< 7.8	< 14.7	557	< 10.1	14.5	< 10.1	0.354	< 10.1	< 0.42	< 9.74
300309525	TC 2 10 6	< 7.8	< 14.7	870	< 10.1	14.8	< 10.1	0.421	< 10.1	< 0.42	< 9.74
300309526	TC 2 10 7	< 7.8	< 14.7	1190	< 10.1	14	< 10.1	0.44	< 10.1	< 0.42	< 9.74
300309527	TC 2 10 8	< 7.8	< 14.7	1720	< 10.1	14.9	< 10.1	0.501	< 10.1	< 0.42	< 9.74
300309528	TC 2 10 9	< 7.8	< 14.7	1150	< 10.1	14.4	< 10.1	0.394	< 10.1	< 0.42	< 9.74
300309529	TC 2 10 10	< 7.8	< 14.7	1310	< 10.1	14	< 10.1	0.462	< 10.1	< 0.42	< 9.74
300309530	TC 2 10 11	< 7.8	< 14.7	989	< 10.1	15.2	< 10.1	0.404	< 10.1	< 0.42	< 9.74
300309531	TC 2 10 12	< 7.8	< 14.7	1240	< 10.1	14.3	< 10.1	0.464	< 10.1	< 0.42	< 9.74
Relative Standard Deviation		(N/A % RSD)	(N/A % RSD)	(10 -11 % RSD)	(N/A % RSD)	(N/A % RSD)	(N/A %RSD)	(10 -11 % RSD)	(N/A % RSD)	(N/A % RSD)	(N/A % RSD)

Table 14 (continued). Cation and anion leachate results for depth discrete-subsample cut from Sample Tc2-10 cured at ambient temperature in a humid environment. A “fresh” surface was subsequently exposed to and leached in DI water.

3/13/2014 12:41	Sample	V	Zn	Zr	Bromide	Chloride	Fluoride	Formate	Nitrate	Nitrite	Oxalate	Phosphate	Sulfate
ADS No.	No.	mg/L	mg/L	mg/L	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL	µG/mL
300309520	TC 2 10 1	0.154	< 0.2	< 2.2	<20	<10	<20	<20	153	36	<10	<10	143
300309521	TC 2 10 2	0.138	<	< 2.19	<20	25	<20	<20	1120	264	<10	<10	552
300309522	TC 2 10 3	0.32	<	< 2.19	<20	43	<20	<20	2780	685	<10	<10	1080
300309523	TC 2 10 4	0.353	<	< 2.19	<20	40	<20	<20	2710	651	<10	<10	1010
300309524	TC 2 10 5	0.401	<	< 2.19	<20	42	<20	<20	2950	707	<10	<10	1140
300309525	TC 2 10 6	0.552	<	< 2.19	<20	62	<20	<20	4360	1090	<10	<10	1710
300309526	TC 2 10 7	0.661	<	< 2.19	<20	80	<20	<20	6060	1480	<10	<10	2300
300309527	TC 2 10 8	0.952	<	< 2.19	<20	112	<20	<20	9320	2250	<10	<10	3370
300309528	TC 2 10 9	0.679	<	< 2.19	<20	78	<20	<20	5740	1430	<10	<10	2250
300309529	TC 2 10 10	0.759	<	< 2.19	<20	86	<20	<20	6900	1660	<10	<10	2260
300309530	TC 2 10 11	0.628	<	< 2.19	<20	67	<20	<20	5170	1230	<10	<10	1930
300309531	TC 2 10 12	0.69	<	< 2.19	<20	82	<20	<20	6530	1550	<10	<10	2410
Relative Standard Deviation		(N/A % RSD)	(N/A % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)	(10 % RSD)	(N/A % RSD)	(N/A % RSD)	(10 % RSD)