

**Contract No:**

This document was prepared in conjunction with work accomplished under Contract No. 89303321CEM000080 with the U.S. Department of Energy (DOE) Office of Environmental Management (EM).

**Disclaimer:**

This work was prepared under an agreement with and funded by the U.S. Government. Neither the U.S. Government or its employees, nor any of its contractors, subcontractors or their employees, makes any express or implied:

- 1 ) warranty or assumes any legal liability for the accuracy, completeness, or for the use or results of such use of any information, product, or process disclosed; or
- 2 ) representation that such use or results of such use would not infringe privately owned rights; or
- 3) endorsement or recommendation of any specifically identified commercial product, process, or service.

Any views and opinions of authors expressed in this work do not necessarily state or reflect those of the United States Government, or its contractors, or subcontractors.



**Savannah River  
National Laboratory®**

A U.S. DEPARTMENT OF ENERGY NATIONAL LAB • SAVANNAH RIVER SITE • AIKEN, SC • USA

# **FY2022 Status Report: Model 9975 O-Ring Fixture Long-Term Leak Performance**

**T. T. Truong**

**Z. Lowe**

September 2022

SRNL-STI-2022-00437, Revision 0

SRNL.DOE.GOV

## **DISCLAIMER**

This work was prepared under an agreement with and funded by the U.S. Government. Neither the U.S. Government or its employees, nor any of its contractors, subcontractors or their employees, makes any express or implied:

1. warranty or assumes any legal liability for the accuracy, completeness, or for the use or results of such use of any information, product, or process disclosed; or
2. representation that such use or results of such use would not infringe privately owned rights; or
3. endorsement or recommendation of any specifically identified commercial product, process, or service.

Any views and opinions of authors expressed in this work do not necessarily state or reflect those of the United States Government, or its contractors, or subcontractors.

**Printed in the United States of America**

**Prepared for  
U.S. Department of Energy**

**Keywords:** 9975

*Viton*

*Service life*

**Retention:** *Permanent*

## **FY2022 Status Report: Model 9975 O-Ring Fixture Long-Term Leak Performance**

T. T. Truong  
Z. Lowe

September 2022

---

Savannah River National Laboratory is operated by  
Battelle Savannah River Alliance for the U.S. Department  
of Energy under Contract No. 89303321CEM000080.



## REVIEWS AND APPROVALS

### AUTHORS:

---

T. T. Truong, Separation Sciences & Engineering	Date
---	------

---

Z. Lowe, Separation Sciences & Engineering	Date
--	------

### TECHNICAL REVIEW:

---

B. Lewczyk, Biological & Analytical Sciences	Date
--	------

### APPROVAL:

---

R. E. Fuentes, Pu Surveillance Program Lead, Separation Sciences & Engineering	Date
---	------

---

M. M. Reigel, Manager Separation Sciences & Engineering	Date
--	------

---

F. M. Pennebaker, Manager Chemical Processing & Characterization	Date
---	------

---

A. J. O'Grady, KAC Process Support Engineering	Date
--	------

---

D. R. Leduc, Packaging Technology	Date
-----------------------------------	------

## EXECUTIVE SUMMARY

Leak testing experiments to monitor the aging performance of Viton<sup>®</sup> GLT and GLT-S O-rings used in the model 9975 shipping package has been ongoing since 2004 at Savannah River National Laboratory. Seventy tests using mock-up 9975 primary containment vessels (PCVs) with GLT O-rings were assembled and heated to temperatures ranging from 200 to 450 °F. Due to material substitution, fourteen tests with GLT-S O-rings were initiated in 2008 and heated to temperatures ranging from 200 to 400 °F. The conditioning temperatures are elevated compared to the calculated maximum O-ring temperature in a 9975 package in storage, 158 °F, to accelerate aging and enable observations of O-ring failures in a reasonable time frame.

The fixtures are leak tested periodically and all GLT O-ring fixtures aging at 350 °F or above have failed to maintain a leak-tight seal. Eight GLT O-ring fixtures aging at 300 °F have failed after 2.8 to 5.7 years at temperature while the remaining fixtures at 300 °F were retired from testing following more than five years without failure. There has been one GLT O-ring fixture which failed after 13.4 years aging at 200 °F. However, 20 other GLT O-rings aging at 200 °F have remained leak-tight for over 14 years and remain in test. No failures have yet been observed in GLT O-ring fixtures aging at 270 °F for 10.4 years. All GLT-S O-ring fixtures aging at 300 °F or above have failed their leak test. No failures have yet been observed in GLT-S O-ring fixtures aging at 250 °F for 12.5 years. This year, one GLT-S O-ring fixture failed after 12.4 years aging at 200 °F.

Data from the O-ring fixtures are generally consistent with results from compression stress-relaxation testing, and provide confidence in the predictive models based on those results. However, uncertainty exists in extrapolating these elevated temperature results to the lower temperatures of interest for normal storage in K-Area Complex (KAC). Oxygen consumption testing, which includes results from temperatures near KAC normal storage temperatures, is ongoing to provide further confidence and corroborate these extrapolations. The collective data from these test efforts suggest the minimum O-ring service life at KAC normal storage conditions should be at least 34 years for GLT and GLT-S O-rings.

Measurement of compression set in O-rings removed from failed fixtures, compared to that from KAC surveillance O-rings, indicate significant margin remains for O-rings still in service in 9975 packages in KAC. Aging and periodic leak testing will continue for the remaining 25 mock-up PCV fixtures.

## TABLE OF CONTENTS

LIST OF TABLES .....	vii
LIST OF FIGURES .....	vii
LIST OF ABBREVIATIONS .....	viii
1.0 Introduction .....	1
2.0 Experimental Procedure .....	1
2.1 Fixture assembly and conditioning .....	1
2.2 Irradiation .....	2
2.3 Leak Testing .....	2
2.4 Test Matrix .....	2
3.0 Results and Discussion .....	4
4.0 Conclusions .....	9
5.0 References .....	10
Appendix A . Supplemental Information .....	A-1

## LIST OF TABLES

<b>Table 1.</b> Summary of fixture status and test parameters .....	3
<b>Table 2.</b> Summary of GLT and GLT-S O-ring leak failures .....	4
<b>Table 3.</b> Leak rate data since last status report.....	8

## LIST OF FIGURES

<b>Figure 1.</b> Pictures of (a) mock-up PCV test fixture lid and body and (b) assembled fixture with heater and insulation. ....	2
<b>Figure 2.</b> (a) Picture of fixture 13H prior to removal of the O-rings from the plug showing no discernible spring back. Pictures of O-rings (b) in the plug and (c) removed from the plug. ....	5
<b>Figure 3.</b> Compression set values for field surveillance PCV O-rings and failed fixture O-rings within one hour of opening vessel. ....	6
<b>Figure 4.</b> Summary of behavior for fixtures still in test and those that failed the leak test. The trendline illustrates a lower bound projection based upon failure data. ....	7
<b>Figure 5.</b> Extrapolations of O-ring results for leak testing and compression stress-relaxation. The extrapolated segments shown by dashed lines are only partially supported by data which did not reach a failure condition. ....	7

## **LIST OF ABBREVIATIONS**

CSR	Compression stress-relaxation
DE	Destructive examination
KAC	K-Area Complex
PCV	Primary containment vessel
SARP	Safety Analysis Report for Packaging
SCV	Secondary containment vessel
SRNL	Savannah River National Laboratory
SRS	Savannah River Site

## 1.0 Introduction

Special nuclear materials are stored within model 9975 shipping packages in the K-Area Complex (KAC) at the Savannah River Site (SRS). The 9975 shipping package consists of a 35 gallon stainless steel drum, Celotex<sup>®</sup> fiberboard insulation, lead shield, and primary and secondary containment vessels. The 9975 shipping package design, performance, and analysis for safe transport of radioactive material are described in the Safety Analysis Report for Packaging (SARP) [1]. The primary and secondary containment vessels (PCV and SCV) are sealed with dual Viton<sup>®</sup> GLT or GLT-S fluoroelastomer O-rings. The outer O-rings are credited with being leak-tight while in transport. The 3013 container is credited with providing containment of special nuclear materials while stored inside a 9975 package. For non-3013 containers stored in a 9975 package, the containment vessel outer O-rings are credited with maintaining containment [2]. The SRS Surveillance Program monitors material performance to establish a basis for service life and ensures the continued integrity of 9975 packages [3-4].


O-ring seals were identified as susceptible to aging and degradation under storage conditions, and experiments to monitor the aging performance of GLT O-rings has been ongoing since 2004 at Savannah River National Laboratory (SRNL). Due to loss of availability, the O-rings were substituted with GLT-S polymers and tests with GLT-S O-rings were initiated in 2008. The experiments include leak testing, compression stress-relaxation (CSR) and oxygen consumption testing [5-6]. The experiments evaluate the performance of O-rings, conditioned at elevated temperatures, to predict their service life in 9975 packages stored in KAC. The leak performance of O-rings is evaluated by periodically leak testing mock-up PCV fixtures after conditioning at elevated temperatures. The 9975 shipping package is currently approved for a storage period of 40 years with 3013 and 20 years with non-3013 containers in KAC [7-9].

Long-term testing of O-ring leak performance has been previously reported; reference 6 summarized experimental results of Viton<sup>®</sup> O-rings through July 2021. This report presents the data collected since the previous status report through August 2022.

## 2.0 Experimental Procedure

### 2.1 Fixture assembly and conditioning

Test fixtures were assembled with either Parker Seals V0835-75 (Viton<sup>®</sup> GLT) O-rings or Parker Seals VM835-75 (Viton<sup>®</sup> GLT-S) O-rings in a mock-up PCV. The assembly and setup have been described in detail in previous reports [10-11]. The two-piece lid of the mock-up PCV was machined to be identical to the actual PCV lid used in the 9975 shipping package. The body of the mock-up PCV is 3.5 inches tall with a thread hole machined in the bottom to provide a port for evacuating and filling the vessel with gas. A PCV test fixture with the O-rings installed in the lid is shown in Figure 1a. The mock-up PCV fixtures were assembled per the requirements described in the SARP [1]. The fixture is heated with a flexible heater and capped with insulation at the exposed ends. The assembled fixture is shown in Figure 1b. The assembled fixture was leak tested initially to confirm leak-tightness before conditioning at 200, 250, 270, 300, 350, 400, or 450 °F.

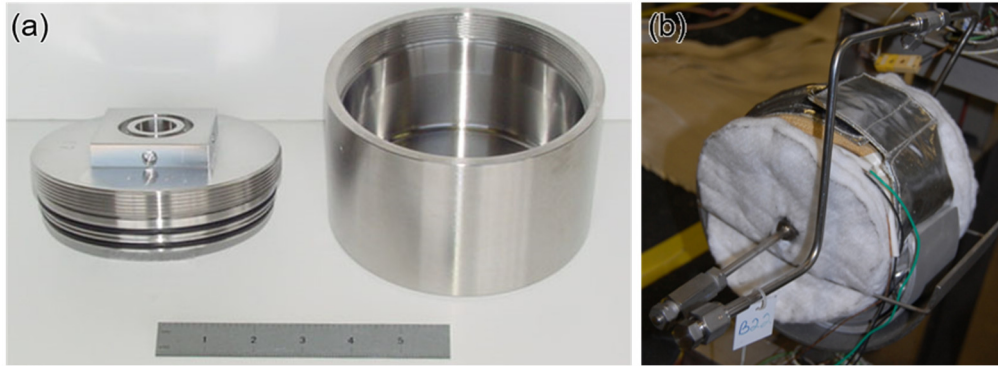

**Figure 1.** Pictures of (a) mock-up PCV test fixture lid and body and (b) assembled fixture with heater and insulation.

## 2.2 Irradiation

If the fixture required irradiation, it was placed in a Co-60 gamma cell and irradiated at one of two dose rates to reach a total dose of 2 E5 rad. This is equivalent to a ten year dose at the bounding dose rate expected for the PCV O-rings (2 rad/hr). The fixture was irradiated at either a “slow” dose rate of approximately 667 to 830 rad/hr (lasting ~240 hours) or a faster rate of ~1.7 E5 rad/hr (lasting 72 minutes), as Viton® and other polymers are known to be sensitive to dose rate. After irradiation, the fixture was leak tested again to ensure that irradiation alone did not affect leak-tightness, and then heated to conditioning temperature.

Additional irradiations were performed in 2014 and 2018 to maintain an approximate balance relevant to storage conditions between the thermal and radiation degradation mechanisms. The fixtures were leak tested pre- and post-irradiation. Three fixtures received an additional 2 E5 rad (at high dose rate) and will continue to receive an additional 2 E5 rad every four years, and three other fixtures received an additional 1 E5 rad (at high dose rate) and will continue to receive an additional 1 E5 rad every four years. As of August 2022, three fixtures have a total dose of 6 E5 rad and three fixtures have a total dose of 4 E5 rad.

## 2.3 Leak Testing

The O-ring fixtures are leak-tested after initial setup, after irradiation, and periodically after conditioning at elevated temperatures to the same leak-tight criterion as the 9975 PCV and SCV O-rings. The fixtures are leak tested per ANSI standard N14.5-97 at room temperature, generally between 68-77 °F, using a Varian 959 helium mass spectrometer leak detector [12]. Fixtures with leakage rates less than 1 E-7 ref·cc/sec air (or 2 E-7 ref·cc/sec He) are considered leak-tight. A gas filled envelope test, as defined in ANSI N14.5-97, is used for the mock-up PCV fixtures. Both O-rings are tested simultaneously with failure of either O-ring causing a failure of the test. Although this approach differs from annual certification testing, it gives results that are valid and comparable, and accommodates the difference in set up of the actual PCV and SCV and the mock-up PCV fixture. If a leak is found, it is possible to determine which O-ring (*i.e.*, inner and/or outer O-ring) is leaking by selectively directing the helium to either the interior or exterior of the fixture.

## 2.4 Test Matrix

Eighty-four fixtures have been assembled and evaluated since 2004 in three test matrices. The first test matrix was developed to determine the importance and effect of several variables on the condition of the GLT O-rings over time inside the KAC storage facility. The variables investigated include O-ring temperature, radiation/dose rate, and O-ring lubrication, and are detailed in Table A-1. There are 62 fixtures and 22 separate sets of conditions in the first test matrix. Fixtures for the second test matrix were assembled using GLT O-rings in 2008 and aged at temperatures ranging from 350 to 450 °F. They were intended to provide some O-ring failures in a shorter time frame and to determine the time to failure at the vendor’s maximum service temperature of 400 °F. The third test matrix investigated the leak performance of GLT-S

O-rings using 14 fixtures and seven separate sets of conditions. Fewer fixtures were used for this alternate O-ring material since it was expected they would demonstrate the same parametric variations as the GLT O-rings. The status of these fixtures along with their test parameters is summarized in Table 1. Experimental activities and analysis are documented in an electronic laboratory notebook [13].

**Table 1.** Summary of fixture status and test parameters

	Temperature (°F)	Gamma dose (rad), dose rate <sup>†</sup>	Lubricant	Fixture ID still in test	Fixture ID removed from test		
					Failed leak test	Retired July 2012	For other reasons**
<b>GLT O-rings</b>	1 <sup>st</sup> Test Matrix	200	~2 E5, High	Silicone <sup>‡</sup>	5, 6, 27, 36, 37, 40		15, 16, 23, 24
		200	~2 E5, High +periodic 2 E5	Silicone	9, 41, 42		
		200	~2 E5, High +periodic 1 E5	Silicone	53, 54, 55		
		200	~2 E5, Low	Silicone	10, 11		
		200	None	Silicone	1, 3, 44, 56, 57	43	13, 28, 29
		300	~2 E5, High	Silicone		8, 12, 26, 31	7, 52
		300	~2 E5, High +2.8 E6 after retirement	Silicone		51	
		300	~2 E5, Low	Silicone		32	18, 30*
		300	None	Silicone		49, 33	4, 61
		300	~2 E5, High	None			2, 14, 48, 50, 62
		300	~2 E5, High	None			19
		300	None	None			34
		200	None	Krytox <sup>®</sup>	35		
		300	~2 E5, Low	Krytox <sup>®</sup>		20	
	2 <sup>nd</sup> Test Matrix	270	None	Silicone	14W, 21W		
		350	~2 E5, High	Silicone		18D	
		350	None	Silicone		19D	
		400	~2 E5, High	Silicone		14D	
		400	None	Silicone		21D	
		450	~2 E5, High	Silicone		23D	
<b>GLT-S O-rings</b>	3 <sup>rd</sup> Test Matrix	200	None	Silicone	15H	13H	
		250	None	Silicone	22H, 16H		
		300	None	Silicone		29H, 34H	
		350	None	Silicone		38H, 39H	
		400	None	Silicone		45H, 58H, 60H, 62H	
		400	2 E5, High	Silicone		28H, 50H	

<sup>†</sup> Low dose rate: 667-830 rad/hr. High dose rate: ~1.7 E5 rad/hr

<sup>‡</sup> Lubricant is silicone high-vacuum grease as specified in assembly of 9975 package [14]

\* Fixture 30 has 1 failed O-ring (inner).

\*\* Other reasons fixtures were removed from test include high temperature leak test difficulties (11 fixtures), and unplanned temperature excursion (14 fixtures) [15].

### 3.0 Results and Discussion

PCV fixtures have been assembled and aged at 200 – 450 °F to identify the time to failure of GLT O-rings (70 tests) and GLT-S O-rings (14 tests). A total of 22 GLT O-ring fixtures and 3 GLT-S O-ring fixtures remain in test. GLT-S O-ring fixture 13H, conditioned at 200 °F, was found not leak-tight after 12.4 years. The inner O-ring failed the leak test, however, it was not conclusive if the outer O-ring failed due to high background reading. This is the first GLT-S O-ring fixture conditioning at 200 °F to fail to remain leak-tight and the second sample after #43, a GLT O-ring fixture, to fail at 200 °F. The other 58 fixtures were retired or failed previously as summarized in Table 1. The times to failure for each O-ring fixture are summarized in Table 2 and plotted in Figure A-1.

Besides fixtures 13H and 43, all of the other 21 O-ring fixtures conditioning at 200 °F have remained leak-tight, with total times at temperature surpassing 12.5 years; the majority of these fixtures are leak-tight after 14 to 16 years (Table 3). Two GLT fixtures began conditioning at 270 °F in 2011. They have remained leak-tight with total time at temperature of 10.4 and 10.7 years at the time of their last leak test. GLT O-rings in the remaining fixtures aging at 300 °F and higher were retired or failed previously, as noted in prior status reports. The other GLT-S O-ring fixtures conditioning at 200 °F or 250 °F have remained leak-tight after 12.5 years. GLT-S O-rings aging at 300 °F and higher have failed previously, as noted in prior status reports. The times to failure for each fixture are summarized in Table 2. Leak rate histories can be found in Table 3 for fixtures in test since the last status report in 2021.

**Table 2.** Summary of GLT and GLT-S O-ring leak failures


	Fixture ID	Temp. (°F)	Days at temperature to failure*	
			Inner O-ring	Outer O-ring
GLT O-ring Fixtures	43	200	4735 - 4884	4735 - 4884
	8	300	2009 - 2082	2009 - 2082
	12	300	957 - 1020	957 - 1020
	26	300	1273 - 1366	1261 - 1273
	30	300	1279 - 1392	1902 - no failure
	31	300	1280 - 1291	1280 - 1291
	32	300	1271 - 1352	1271 - 1352
	33	300	1360 - 1466	1924 - 1979
	49	300	1101 - 1276	1323 - 1360
	18D	350	481 - 497	304 - 324
	19D	350	573 - 594	560 - 571
	14D	400	29 - 45	29 - 45
	21D	400	8 - 28	8 - 28
	23D	450	10 - 12	0 - 8
GLT-S O-ring Fixtures	13H	200	4377 - 4525	4377 - 4525
	29H	300	2370 - 2455	2370 - 2455
	34H	300	2013 - 2096	2013 - 2096
	38H	350	338 - 358	338 - 358
	39H	350	95 - 114	95 - 114
	45H	400	65 - 99	14 - 33
	58H	400	62 - 75	62 - 75
	60H	400	33 - 50	33 - 50
	62H	400	34 - 50	34 - 50
	28H	400	33 - 50	33 - 50
	50H	400	260 - 281	260 - 281

\*The first time at temperature is the last successful leak test and the second time is the failed leak test. Failure occurred at some point between these two times.

The first GLT-S O-ring fixture conditioning at 200 °F to fail after 12.4 years, 13H, was opened to examine the aged O-rings. The O-rings showed no discernable spring back within 7 minutes of opening the fixture as shown in Figure 2a. Subsequent dimensional measurements were used to calculate compression set. Compression set measures the amount of O-ring deformation after removal of force and was calculated using ASTM D395, Method B, as

$$\text{compression set (\%)} = (t_i - t_f) / (t_i - \text{groove depth}) * 100$$


where  $t_i$  and  $t_f$  are the initial and final radial thicknesses, respectively. If the initial radial thickness was not recorded, then the nominal thickness 0.139 inch was assumed. The groove depth for all fixtures is 0.0995 inch. A new O-ring should have a compression set of approximately 0% while a heavily degraded O-ring will have a compression set approaching 100%. Within twenty minutes after opening fixture 13H, the compression set was 58% and 72% for the inner and outer O-rings, respectively. Compression set values were 51% and 65% after one week and slightly decreased to 45% and 56% after 5 weeks. These values of compression set are consistent with those seen in previous failed fixtures as shown in Figure 3.

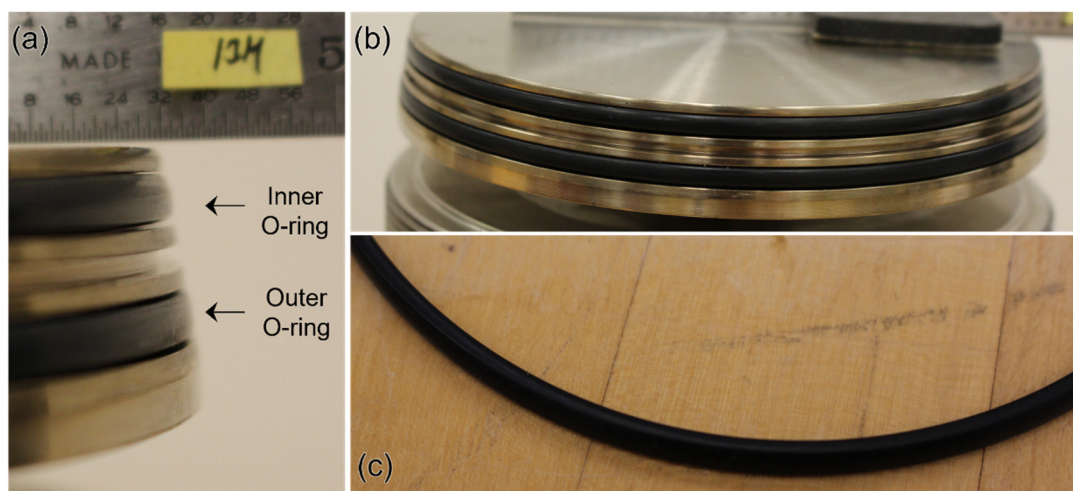

**Figure 2.** (a) Picture of fixture 13H prior to removal of the O-rings from the plug showing no discernible spring back. Pictures of O-rings (b) in the plug and (c) removed from the plug.

Additional observations of fixture 13H include the O-rings were adherent to the plug and the fixture body. The O-rings have flat and rounded surfaces on opposite sides (Figure 2). The O-rings were black and there were minimal stains on the plug and fixture body (Figure A-2). No defects were visually observed on the O-rings. In contrast to fixture 43 (failed after 13.4 years at 200 °F), there was no visible grease around the threads of the plug or on the O-rings, nor any stains on the O-rings. Furthermore, fixture 13H was not rectangular like fixture 43 with compression set above 90% after 4 weeks. It is not known at this time the cause of leak test failure for fixture 13H. The other GLT-S O-rings aging at 200 °F remain in test after passing the leak test at 12.5 years.

As noted in previous reports, sufficient data are available to compare the time to failure for GLT and GLT-S O-rings at three temperatures. At 300 °F and 400 °F, most of the GLT-S O-ring fixtures remained leak-tight longer than the GLT O-ring fixtures. At 350 °F, the trend is reversed, with GLT O-rings remaining leak-tight longer than the GLT-S O-ring fixtures. With the scatter in this varying trend, it is not practical to conclude whether one O-ring material would perform better than the other, especially at the lower temperatures typical of storage service. This conclusion remains unchanged from the previous status report.

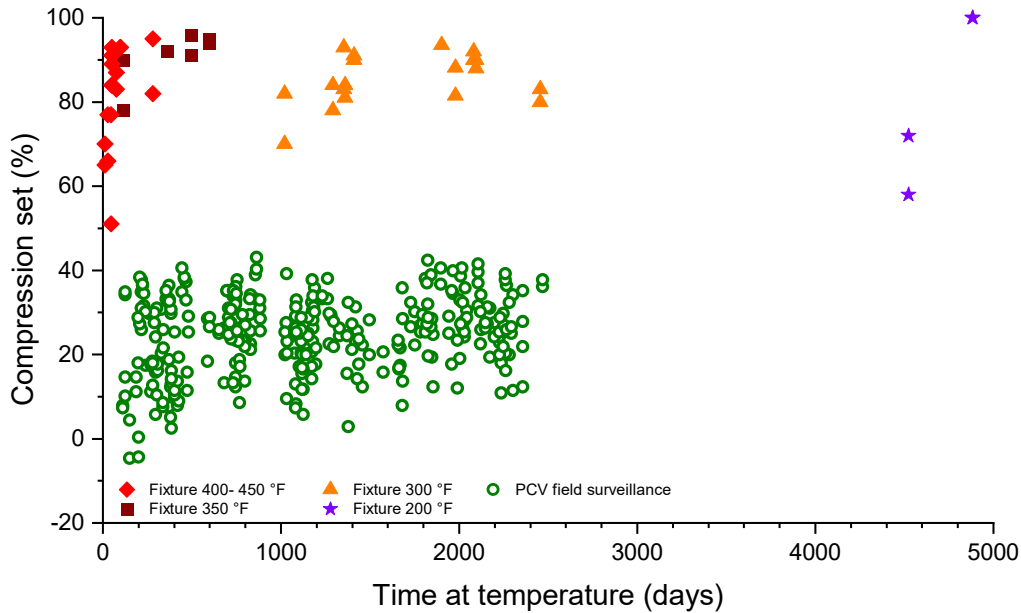


**Figure 3.** Compression set values for field surveillance PCV O-rings and failed fixture O-rings within one hour of opening vessel.

No influence on time to failure has been observed from the irradiations performed on test fixtures. Six fixtures received additional irradiation in 2018 and will continue to receive an additional dose every four years. As of August 2022, three fixtures have a total dose of 6 E5 rad and three fixtures have a total dose of 4 E5 rad (Table 3). It is recognized that these irradiations present a simplistic approach that ignores potential synergistic effects from the simultaneous exposure to elevated temperature and radiation.


Recent thermal analysis of the 9975 package used 95 °F as the long-term average ambient temperature in KAC [16]; based on the storage temperature history of KAC, 95 °F is a conservatively bounding average ambient temperature [17]. For a package with a maximum heat load of 19 W, the calculated O-ring temperature is 156 °F at beginning of life and 158 °F after 20 years of service with bounding package degradation [16]. Figure 4 depicts the time at temperature for fixtures that failed the leak test and those that are still in test. A trendline provides a lower bound to the failure data to illustrate a potential extrapolation of the observed behavior. O-rings aging at 250 °F and 270 °F have exceeded the lower bound trendline; these O-rings have been conditioning at temperature for over 10.4 years. These O-rings demonstrate that the trendline maintains a lower bound to leak test data at least to 250 °F. Furthermore, there are 21 (GLT and GLT-S) O-ring fixtures aging at 200 °F that have maintained a leak-tight seal for over 12.5 years, exceeding the observed 12.4 years to failure for fixture 13H. The degree of scatter in the data would suggest significant uncertainty for extrapolations over a large temperature range. Nevertheless, this trendline suggests the possibility that O-rings aging at 158 °F (KAC storage temperature) might maintain a leak-tight seal for up to 59 years.

Figure 5 shows the lower bound trendline from leak testing results and predictions from compression stress-relaxation (CSR) data [5]. The dashed lines extrapolate the O-ring behavior through temperatures for which partial data exist (*i.e.*, samples have not yet reached a failure point). Given the range of scatter observed in both leak testing and CSR testing, it is recommended that any extrapolated service life estimates not exceed the minimum of these projections. CSR results indicate GLT and GLT-S O-rings will perform their required function in KAC storage conditions for at least 34 years. As additional data are collected, and the aging models refined, these service life estimates may be revised. However, at present, both GLT and GLT-S O-rings are expected to provide leak-tight seals well in excess of the current approved 20 year KAC service life for 9975 packages with non-3013 containers.

The compression set of PCV O-rings in 9975 packages in KAC were measured previously during field surveillance and presented in Figure 3 along with the values from failed leak testing O-ring fixtures. There is clear separation in compression set values for surveillance O-rings and failed fixture O-rings; failed fixture O-rings have compression set values greater than 50%. While there are no data to specifically show how long it will take at storage conditions for the compression set to increase to that seen from failed test fixtures, if surveillance O-rings continue to show similar behavior, they likely retain significant margin to reaching a failure condition.

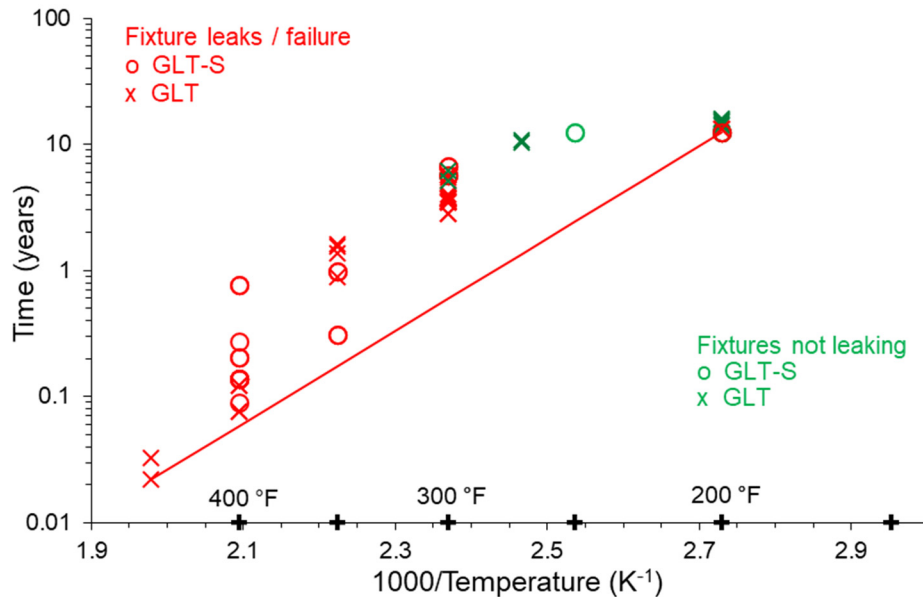

**Figure 4.** Summary of behavior for fixtures still in test and those that failed the leak test. The trendline illustrates a lower bound projection based upon failure data.

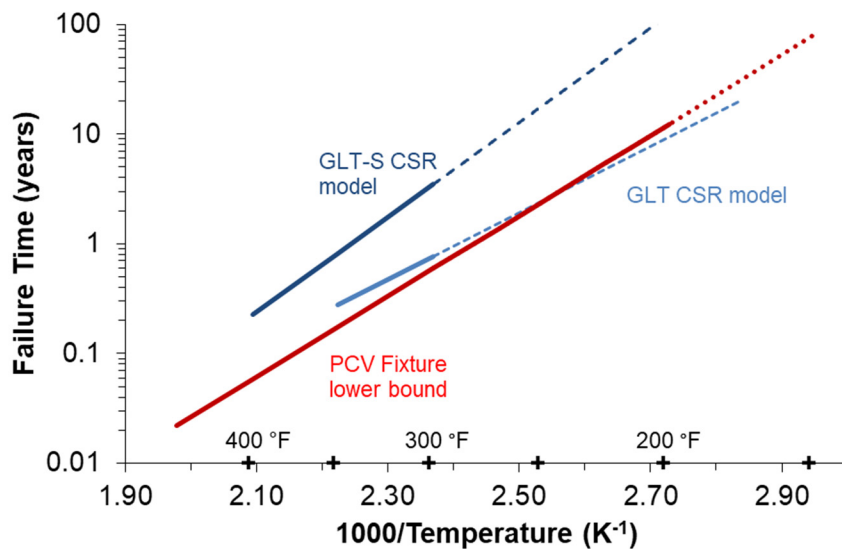

**Figure 5.** Extrapolations of O-ring results for leak testing and compression stress-relaxation. The extrapolated segments shown by dashed lines are only partially supported by data which did not reach a failure condition.

**Table 3.** Leak rate data since last status report

	Fixture ID	Temperature (°F)	Total $\gamma$ dose (rad), dose rate <sup>†</sup>	Lubricant	Date of leak test	Time at temp. (yr)	Leak rate (std cc He/sec)
GLT O-rings	1	200	None	Silicone	8/5/21	15.0	3.8 E-09
					2/15/22	15.5	1.1 E-08
					8/17/22	16.0	3.8 E-09
	3	200	None	Silicone	1/4/22	15.5	2.5 E-08
					6/14/22	15.9	<2.8 E-09
					7/6/22	16.0	1.2 E-08
	5	200	2 E5, High	Silicone	9/28/21	15.0	2.0 E-07*
					9/30/21	15.0	<2.6 E-09
					3/29/22	15.5	1.2 E-08
					4/1/22	15.5	2.5 E-09
	6	200	2 E5, High	Silicone	8/17/21	14.9	1.0 E-08
					3/1/22	15.5	9.3 E-09
	9	200	6 E5, High	Silicone	12/14/21	14.5	3.7 E-09
	10	200	2 E5, Low	Silicone	1/4/22	15.0	7.2 E-09
					6/14/22	15.4	8.0 E-09
					7/6/22	15.5	1.2 E-08
	11	200	1.4 E5, Low	Silicone	2/8/22	15.0	6.3 E-08
					8/17/22	15.5	3.8 E-09
	27	200	2 E5, High	Silicone	9/28/21	13.5	1.3 E-08
					3/29/22	14.0	1.2 E-08
	35	200	None	Krytox <sup>®</sup>	8/17/21	14.5	1.6 E-08
					3/1/22	15.0	9.3 E-09
	36	200	2 E5, High	Silicone	8/5/21	14.5	1.5 E-08
					2/15/22	15.0	5.3 E-09
					8/17/22	15.5	7.6 E-09
	37	200	2 E5, High	Silicone	8/17/21	14.5	1.2 E-08
					3/1/22	15.0	6.2 E-09
	40	200	2 E5, High	Silicone	12/14/21	14.5	1.5 E-08
	41	200	6 E5, High	Silicone	2/8/22	15.0	1.7 E-08
					8/17/22	15.5	3.8 E-09
	42	200	6 E5, High	Silicone	1/25/22	15.0	1.1 E-08
					7/19/22	15.4	7.7 E-09
	44	200	None	Silicone	1/4/22	15.0	1.1 E-08
					1/25/22	15.0	1.8 E-08
					6/14/22	15.4	8.0 E-09
					7/6/22	15.4	1.2 E-08
	53	200	4 E5, High	Silicone	1/25/22	15.0	2.1 E-08
					7/19/22	15.4	7.7 E-09
	54	200	4 E5, High	Silicone	10/5/21	14.7	1.2 E-08
					1/25/22	15.0	4.2 E-08
					7/19/22	15.4	1.2 E-08

	Fixture ID	Temperature (°F)	Total $\gamma$ dose (rad), dose rate <sup>†</sup>	Lubricant	Date of leak test	Time at temp. (yr)	Leak rate (std cc He/sec)
GLT O-rings	55	200	4 E5, High	Silicone	8/5/21	14.5	7.6 E-09
					2/15/22	14.8	<1.8 E-09
					8/17/22	15.3	7.6 E-09
	56	200	None	Silicone	9/28/21	14.5	1.7 E-08
					10/19/21	14.5	3.6 E-09
					3/29/22	15.0	1.2 E-08
					4/1/22	15.0	4.9 E-09
	57	200	None	Silicone	8/17/21	14.5	4.1 E-09
					3/1/22	15.0	3.1 E-09
	14W	270	None	Silicone	8/31/21	9.6	1.1 E-08
					10/19/21	9.7	1.4 E-08
					1/25/22	10.0	8.1 E-08
					4/19/22	10.2	1.8 E-08
					4/25/22	10.2	2.1 E-08
					4/28/22	10.2	2.8 E-09
					7/19/22	10.4	3.9 E-09
	21W	270	None	Silicone	9/28/21	10	1.3 E-08
					1/4/22	10.2	1.4 E-08
					3/29/22	10.5	1.2 E-08
					7/6/22	10.7	7.9 E-09
GLT-S	13H	200	None	Silicone	10/19/21	12.0	1.4 E-08
					4/25/22	12.4	1.0 E-06**
	15H	200	None	Silicone	9/28/21	12.0	1.3 E-08
					3/29/22	12.5	3.0 E-09
	16H	250	None	Silicone	2/8/22	12.0	1.4 E-08
					8/17/22	12.5	7.6 E-09
	22H	250	None	Silicone	11/23/21	12.0	3.4 E-09
					5/25/22	12.5	3.4 E-09

<sup>†</sup> Low dose rate: 667-830 rad/hr. High dose rate: ~1.7 E5 rad/hr

\* Apparent failure of O-rings. Both O-rings passed subsequent test

\*\* O-rings failed

## 4.0 Conclusions

Fixtures for GLT and GLT-S O-rings aging at 300 °F and above have experienced leak test failures or have been removed from test. There have been two observed leak test failures for samples aging at 200 °F after 12.4 years and 13.4 years for GLT-S and GLT O-rings, respectively. However, 21 other GLT and GLT-S O-ring fixtures aging at 200 °F have maintained a leak-tight seal for over 12.5 years, most over 14 years, and remain in test. No failures have yet been observed in GLT O-ring fixtures aging at 270 °F for 10.4 years. For GLT-S O-rings, no failures have been observed for fixtures aging at 250 °F for up to 12.5 years. These 25 fixtures remain conditioning at elevated temperatures and will be periodically leak tested.

The PCV O-ring temperature expected in KAC is 156-158 °F based on an average ambient temperature of 95 °F and maximum payload of 19 W. The leak testing data to date suggest the GLT and GLT-S O-rings aging in KAC storage at temperatures of 158 °F might maintain a leak-tight seal for up to 59 years. Further consideration should be given to results from CSR testing which predict service life of up to 34 years. Measurement of compression set in O-rings removed during KAC surveillance, compared to failed fixtures,

indicates margin remains for O-rings still in service in KAC. Both GLT and GLT-S O-rings are expected to provide leak-tight service in excess of the current approved 20 year KAC storage life for 9975 packages with non-3013 containers.

Aging and periodic leak testing will continue for the remaining 25 fixtures.

## 5.0 References



1. "Safety Analysis Report for Packaging Model 9975", Savannah River Nuclear Solutions, S-SARP-G-00003, Rev. 4, 2015.
2. "K-Area Complex Documented Safety Analysis", Savannah River Nuclear Solutions, WSRC-SA-2002-00005, Rev. 16, 2021.
3. Escobar, A. J., "Savannah River Site Surveillance Program for the Storage of 9975/3013 Plutonium Packages in KAC", Savannah River Nuclear Solutions, WSRC-TR-2001-00286, Rev. 10, 2021.
4. Kiflu, B. B., "Summary and Matrix: 9975 Shipping Package Qualification Program for Extended Storage of Plutonium in the K-Area Complex", Savannah River Nuclear Solutions, SRNS-TR-2008-00290, Rev. 2, 2016.
5. Truong, T. T.; Daugherty, W. L., "Compression Stress-Relaxation and Oxygen Consumption Behavior of 9975 Shipping Package O-rings", Savannah River National Laboratory, SRNL-STI-2018-00201, 2018.
6. Truong, T. T., "FY2021 Status Report: Model 9975 O-Ring Fixture Long-Term Leak Performance", Savannah River National Laboratory, SRNL-STI-2021-00400, 2021.
7. O'Grady, A. J., "9975 Shipping Package/3013 40 Year Life Extension Summary", Savannah River Nuclear Solutions, G-ESR-K-00253, 2022.
8. Escobar, A. J.; Hensel, S. J., "9975 Shipping Package/non-3013 Container 20 Year Life Extension Summary", Savannah River Nuclear Solutions, G-ESR-K-00231, 2019.
9. "Implementation of the Interim Safe Storage Criteria Program", Savannah River Nuclear Solutions, N-ESR-K-00004, Rev. 29, 2022.
10. Daugherty, W. L., "FY2017 Status Report: Model 9975 O-Ring Fixture Long-Term Leak Performance", Savannah River National Laboratory, SRNL-TR-2017-00257, 2017.
11. Daugherty, W. L.; Truong, T. T., "FY2018 Status Report: Model 9975 O-Ring Fixture Long-Term Leak Performance", Savannah River National Laboratory, SRNL-TR-2018-00166, 2018.
12. Institute, A. N. S., American National Standard for Radioactive Materials - Leakage Tests on Packages for Shipment, New York, NY, 1998.
13. Truong, T. T., Leak Testing of O-ring Fixtures, 2021.
14. "Annual Maintenance and Leak Testing for the 9975 Shipping Package", Savannah River National Laboratory, L9.4-10500, Rev. 28, 2018.
15. Daugherty, W. L.; Stefek, T. M., "Fourth Interim Status Report: Model 9975 PCV O-ring Fixture Long-Term Leak Performance", Savannah River National Laboratory, SRNL-TR-2009-00186, 2009.
16. Kiflu, B. B., "The Initial and 20-year Service Thermal Performances of the 9975 Shipping Packages due to Fire-Drop-Smoldering Accidents in KAC", M-CLC-K-00788, 2017.
17. Kiflu, B. B., "KAC MSA RF-TID Temperature Data Validation", M-ESR-K-00069, 2016.
18. Radder, J. A., "Summary and Matrix: 9975 Shipping Package Qualification Program for Extended Storage of Plutonium in the K-Area Complex", Savannah River Nuclear Solutions, SRNS-TR-2008-00290, Rev. 0, 2008.
19. Norkus, J. K., "Integrated Thermal Analysis of the 9975 Shipping Packages for KAMS Phase 6", Savannah River Nuclear Solutions, S-CLC-K-00194, Rev. 2, 2011.

20. "Safety Analysis Report for Packaging Model 9975 B(M)F-85", Westinghouse Savannah River Compan, WSRC-SA-2002-00008, 2003.
21. "Annual Maintenance and Leak Testing for the 9975 Shipping Package", Savannah River National Laboratory, L9.4-10500, Rev. 2, 2007.

## Appendix A. Supplemental Information

**Table A-1.** Test matrix variables for O-ring fixtures

Variable	Values Tested	Basis for Values Tested
Temperature	200 °F (93 °C)	With loss of ventilation in the KAC facility, the maximum ambient temperature is 137 °F [18], and the corresponding PCV O-ring temperature is 199 °F [19].
	300 °F (149 °C)	The maximum allowable temperature for the PCV O-rings for continuous operation is 300 °F [20].
	270, 350, 400, 450 °F (132, 177, 204, 232 °C)	Elevated temperatures added to increase the likelihood of observing O-ring failures in shorter test periods.
Radiation Dose	2 E5 rad in 72 min	The bounding (high) dose rate for the PCV is 2 rad/hr. A total dose of 2 E5 rad represents ten years of storage (the initial period to be validated).
	Additional periodic 2 E5 rad at high dose rate	Additional dose after 8 years, and every 4 years subsequently, to maintain relative balance between degradation mechanisms (radiation, thermal)
	Additional periodic 1 E5 rad at high dose rate	Additional dose after 8 years, and every 4 years subsequently, to maintain relative balance between degradation mechanisms (radiation, thermal)
	2 E5 rad in >200 hr	Longer-term exposure may reveal the added effect of diffusion-limited oxidation (DLO) that only occurs with long-term exposure (lower dose rate)
	None	Many packages will have little radiation exposure. This also serves as an experimental control.
O-Ring Lubrication	Silicone high-vacuum grease	It is specified in assembly of the 9975 package [14].
	Krytox <sup>®</sup> 240AC	It has been used on 9975 O-rings at DOE facilities. It is used on lid components of the 9975 PCV and SCV [21].
	None	It supplies comparative control data. Also, it is possible that the O-rings may be mistakenly installed without grease.



**Distribution:**

R. J. Bayer, 705-K  
E. G. Estochen, 705-K  
R. E. Fuentes, 773-A  
R. J. Grimm, 705-K  
M. B. Heath, 705-K  
S. J. Hensel, 705-K  
S. L. Hudlow, 705-K  
J. M. Jordan, 705-K  
M. D. Kranjc, 730-A  
D. R. Leduc, 730-A  
B. Lewczyk, 773-A  
J. M. Licea-Yanez, 730-A  
Z. Lowe, 773-51A  
J. W. McEvoy, 707-C  
K. Moeller, 705-K  
A. J. O'Grady, 705-K  
R. A. Osborne, 705-K  
F. M. Pennebaker, 773-A  
M. M. Reigel, 773-A  
L. N. Sebring, 705-K  
T. E. Skidmore, 730-A  
T.T. Truong, 773-41A  
Document Control