

Contract No:

This document was prepared in conjunction with work accomplished under Contract No. 89303321CEM000080 with the U.S. Department of Energy (DOE) Office of Environmental Management (EM).

Disclaimer:

This work was prepared under an agreement with and funded by the U.S. Government. Neither the U.S. Government or its employees, nor any of its contractors, subcontractors or their employees, makes any express or implied:

- 1) warranty or assumes any legal liability for the accuracy, completeness, or for the use or results of such use of any information, product, or process disclosed; or
- 2) representation that such use or results of such use would not infringe privately owned rights; or
- 3) endorsement or recommendation of any specifically identified commercial product, process, or service.

Any views and opinions of authors expressed in this work do not necessarily state or reflect those of the United States Government, or its contractors, or subcontractors.

Synthesis of Metal Oxide Microparticles for Use as Carriers of Intentional Forensic Signatures

James Louis-Jean^{1*}, Rachel Bergin¹, Michael Bronikowski¹, Wendy Kuhne¹, Seth Lawson¹, Abigail Waldron¹, Matthew Wellons¹, Spencer M. Scott¹

¹Savannah River National Laboratory, Aiken SC

*Presenting Author, james.louis-jean@srnl.doe.gov, 803-967-0221

Abstract

The trafficking of illicit and counterfeit materials is a far-reaching problem with significant economic impacts. The development and commercialization of taggant technologies, which can be introduced intentionally into commodity products to trace fraud or diversion through the rapid determination of commodity provenance, has received considerable interest within the context of forensics as a key deterrence strategy. Among the candidate taggant technologies, engineered microparticles (EμPs) offer a promising route for the introduction of intentional forensic signatures due to their highly uniform and tailorable physical and compositional properties. Taggant EμPs are a promising strategy for identifying the provenance of high consequence commodities such as nuclear material, including reactor fuel. Spray drying-based methods offer a facile and scalable route for the synthesis of EμPs with uniform composition, morphology, and particle size distribution. This work investigates the suitability of aerosol-based methods for the manufacture of taggant EμPs using the Savannah River National Laboratory (SRNL)-developed THERmally Evaporated Spray for Engineered Uniform particulateS (THESEUS) system. In this system, uniform droplets of a feedstock solution containing a metal ion of the desired final composition are aerosolized, carried through a tube furnace (up to 1000 °C) for drying and oxide conversion, and collected using an electrostatic precipitator. Metal oxides of early candidate taggants for nuclear fuel (Mo and W) were used as an initial demonstration for the synthesis of taggant EμPs. The uniformity of the generated particles of MoO₃ and WO₃ were assessed using both *in situ* aerodynamic particle sizing measurements, as well as *ex-situ* automated particle analysis using scanning electron microscopy (SEM). The generated particles displayed highly uniform particle size distributions, with geometric standard deviations (σ_G) below 1.25. The material phase of the generated particles was confirmed using a combination of X-ray diffraction and Raman spectroscopy. This work demonstrates a facile route for the manufacture of particles with tailored physical and chemical properties for potential use as taggants in the nuclear fuel cycle.

Introduction

Counterfeiting and illicit trafficking of high-value products present an ongoing problem with significant economic and security impacts. As this challenge persists across industries and throughout global supply chains, there is a need to develop technologies to aid in the discrimination of counterfeit and genuine products and to identify diversion in supply chains. One proposed technique to accomplish this involves the use of taggants. Taggants are markers which can be incorporated into products to provide a means to establish provenance throughout the life cycle of a product, enabling the assessment of material provenance with high confidence.

Numerous methods for the encoding of taggant signatures have been proposed, including optical barcodes, novel chemical complexes and/or ratios, fluorescent additives, nanocrystalline inclusions, DNA barcodes, and isotopic barcodes.¹⁻³ Each of the proposed tagging mechanisms present unique tradeoffs involving their respective resolving power and/or discernability, ease

and/or speed of taggant interpretation, resistance to adulteration, technical maturity, and cost to implement. One proposed method for the introduction of taggants to a product or supply chain involves the use of highly uniform engineered microparticulates (EuPs) with tailored size, material phase, or isotopic composition, in which each particle serves as a carrier of the necessary information to identify the product's origins.¹

This work investigates the synthesis of EuPs via an aerosol-based technique for use as taggants, specifically for nuclear fuel. EuPs offer a facile route for the introduction of taggants for which the taggant signatures are expected to be difficult to obfuscate given the pervasive nature of microparticulates and the sophistication of particle analysis techniques employed in fields such as nuclear safeguards and forensics.⁴⁻⁶ Candidate taggant elements for nuclear fuel include tungsten and molybdenum, based on factors including the material compatibility with uranium oxide, material properties (i.e., melting temperatures), the number of stable isotopes, neutron absorption cross-sections, and the maturity of analytical techniques including mass spectrometry.⁷⁻⁹ Aerosol-based techniques, such as spray drying or spray pyrolysis offer a scalable route for the manufacture of uniform particles with controllable properties such as size, morphology, and material phase, each of which may be further used to encode taggant information.¹⁰ Spray drying techniques have been previously employed in the synthesis of tungsten oxide¹¹⁻¹³ and molybdenum oxide¹⁴⁻¹⁶ particles.

This work leverages recent advances in the Savannah River National Laboratory (SRNL)-developed THERmally Evaporated Spray for Engineered Uniform particulateS (THESEUS) system,^{17, 18} developed for the manufacture of microparticulates with uniform size, material phase, and elemental and isotopic composition, to synthesize uniform particulates of tungsten trioxide (WO₃) and molybdenum trioxide (MoO₃). The demonstrated synthesis capability for uniform taggant particulates with controlled physical and compositional properties will be further explored as a route for the introduction of intentional forensic signatures into nuclear fuel, namely isotopic barcodes.

Experimental Methods

Material Feedstock Preparation

Feedstock solution of molybdic acid (Alfa Aesar CAS #7782-91-4, Lot #10224188, 85-90% purity) was prepared by dissolving the material in ultrapure water at room temperature, while tungstic acid (Alfa Aesar CAS #7783-03-1, Lot #P25F006, 99% purity) solution was prepared using a mixture of 30% H₂O₂ and ultrapure water at 45 °C for 30 min to promote dissolution. The desired feedstock solution concentrations (**Table 1**~~**Table 1**~~) were based on target calcined particle size as calculated using the Flow Focusing Monodisperse Aerosol Generator (FMAG, Model 1520, TSI Inc.) calculator provided by TSI, Inc. Manipulations were conducted using calibrated analytical balances and pipets, with nominal measurement errors of ±0.05 mg and ±0.001 mL, respectively.

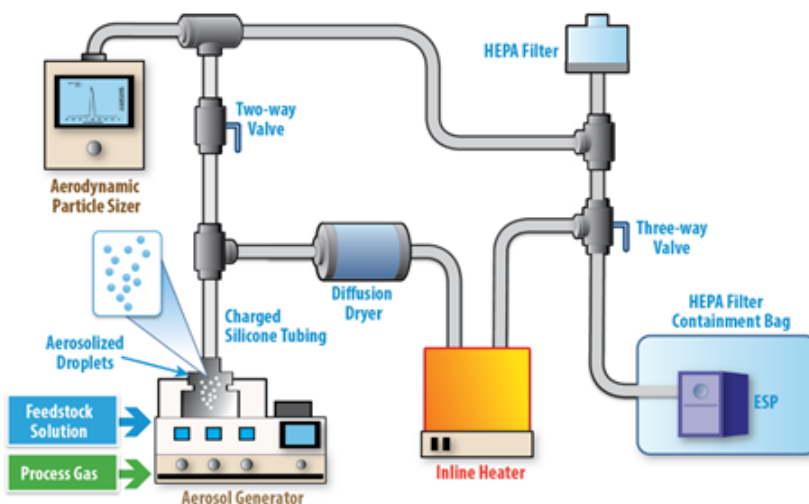
Formatted

Table 1. THESEUS operating conditions for E μ Ps taggants production under constant frequency, solution flow rate, dilution air flow, and flow focusing air pressure.

Feedstock	Conc. (vol/vol)	Target diameter (μ m)	Temp ($^{\circ}$ C)	Target phase
H ₂ MoO ₄ ·xH ₂ O	1.62E-4	1.0	700	MoO ₃
H ₂ WO ₄ ·xH ₂ O	1.25E-4	1.0	800	WO ₃

THESEUS Particle Production

E μ Ps of MoO₃ and WO₃ were produced using the THESEUS system (**Figure 1**~~Figure-1~~).^{17, 18} Droplets of the feedstock solutions were generated via the FMAG at a frequency of 150 kHz with a solution injection rate of 3 mL/h, and a flow-focusing pressure of 2.00 ± 0.05 psi. Filtered air, at a flow rate of 10.0 ± 0.1 L/min was used as a carrier of the aerosolized droplets through the system. The droplets were thermally converted to the desired oxide phases (**Table 1**~~Table-1~~) via inline heating using a tube furnace (Model TF55030C-1, Thermo Fisher Scientific, Inc.) equipped with a 1-inch Inconel 625 tube. The generated particles were collected via an SRNL-designed electrostatic precipitator (ESP)¹⁹ on polished silicon and carbon planchets for small scale (μ g) production or onto electropolished stainless steel plates for milligram-scale powder production. An Aerodynamic Particle Sizer (APS, Model 3321, TSI Inc.) was used to measure *in situ* particle size distributions and assess stability of the system during sustained (multi-day) operations involved in the generation of milligram-scale powder production.

**Figure 1.** Schematic representation of the THERmally Evaporated Spray for Engineered Uniform particulateS (THESEUS) system. Aerosol are formed via the generator, dried, calcined, and collected downstream via ESP.

Characterization

Powder X-ray diffraction (PXRD) measurements were performed at room temperature using Cu K α X-rays (1.5406 Å). Individual particles were characterized using the Renishaw InVia Raman spectrometer, analyzed with a 514 nm laser, 1800 gv/mm grating, and the 1-inch CCD (UV – enhanced deep depletion CCD detector, cooled to -70 $^{\circ}$ C). The particles were viewed under a 100x microscope objective with a 30 s exposure time. Acquisitions were static, centered around 1000 cm^{-1} , giving a range of around 25-1900 cm^{-1} . Power flux studies were completed to evaluate the effect of laser power on particle oxidation with laser intensity controlled by neutral density filters.

to values of 1, 2.5, 5, and 10% power. Based on preliminary characterizations, 2.5 and 5 % power were selected to avoid damage and total ablation of particles. Raman spectra of multiple particles per sample were subsequently processed in Wire 5.1 software for background subtraction and Origin for smoothing.

High-resolution scanning electron microscopy (SEM) measurements were collected using a field emission Tescan Mira 4 (Model S6122) with an accelerating voltage of 5 keV as well as a field emission Carl Zeiss Supra 40VP SEM operated by Zeiss SmartSEM and equipped with an Oxford X-Max 80 mm² detector using Oxford AzTEC software. Automated Particle Measurement (APM) identified particle morphology by signal intensity and elemental composition using energy-dispersive X-ray (EDX) with an accelerating voltage of 20 keV. Reconciliation of APS and APM size distributions was used to estimate the apparent density of the particles by applying an inverse square of density with a shape correction factor of one to the APS data.

Results

Aerodynamic Sizing and Electron Microscopy Characterization

The short residence time in the furnace (0.93 s) and thermal processing of the feedstock material to stable oxide induced noticeable morphological features on the surface of MoO₃ and WO₃ EμPs, as shown in **Figure 2** and **Figure 3**, respectively. Other well-defined parameters showed significant compositional dependence between particle type including aerodynamic size, geometric standard deviations (σ_G), and density (**Table 2**). Both MoO₃ and WO₃ EμPs formed highly spherical particles with monodisperse size distributions, as evidenced by σ_G values below 1.25 in the APS, though MoO₃ particles via SEM exhibited a larger σ_G value. The average ECD was larger than target 1 μm for both particle types (**Table 1**). Correspondingly, the apparent density of these EμPs also fell below value; this is hypothesized as the result of increased porosity and other morphological inconsistencies in particle production.

Table 2. Particulates size comparison of as-generated EμPs taggants along with their associated geometric standard deviation and corrected particle density.

	APS		SEM		Density	
	Aerodynamic size (μm)	Geometric Standard Deviation (σ_G)	APM Average ECD (μm)	Geometric Standard Deviation (σ_G)	Theoretical (g/cm ³)	Calculated (g/cm ³)
MoO ₃	2.20	1.10	1.45	1.33	4.71	2.32
WO ₃	3.11	1.07	1.55	1.25	7.15	4.01

Note: σ_G is unitless; ≤ 1.25 indicates monodisperse and > 1.25 indicates polydisperse aerosol size distribution.

The generated MoO₃ particles have a spherical to spheroidal morphology which exhibit a broad particle size distribution spanning the range of approximately 1-2 μm as displayed by APS and APM-SEM (**Figure 2**). The microporous nature of these particles is hypothesized as resulting from the rapid dehydration of the uniform aerosolized droplet of the feedstock within the furnace, followed by phase transition during sintering of solid particles to yield highly crystalline MoO₃ EμPs. Concurrent formation of different MoO₃ phases could also impact the apparent morphology and density of EμPs. The observed particle porosity, morphological inconsistency and

size distribution of MoO_3 correlates to a reduced particle density (2.32 g/cm^3) compared to that expected (4.71 g/cm^3).²⁰ This decrease in density resulted in larger than anticipated particle size.

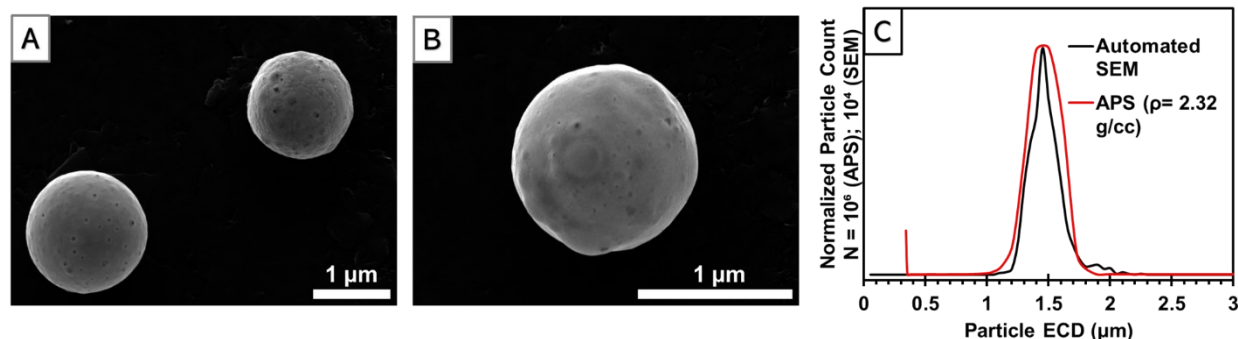


Figure 2. SEM images (A) and (B) of representative MoO_3 particles and particle size comparison (C) by APS and APM-SEM consolidation.

While the WO_3 E μ P_s were produced as uniform spherical particles and as confirmed by their σ_G value, two distinct particulate morphologies were observed within their population. Based on SEM image analysis, the rough textured surface observed on some of the particles, likely the result of rapid dehydration of the aerosolized tungstic acid feedstock, did not produce a noticeable change in particle diameter compared to the smooth spherical particles (**Figure 3**). Calculated density of generated WO_3 E μ P_s is estimated as 4.01 g/cm^3 from reconciliation of APS and APM-SEM particle size distributions (**Figure 3**), consistent with about 56.1% of theoretical density (7.15 g/cm^3) of bulk material.²¹

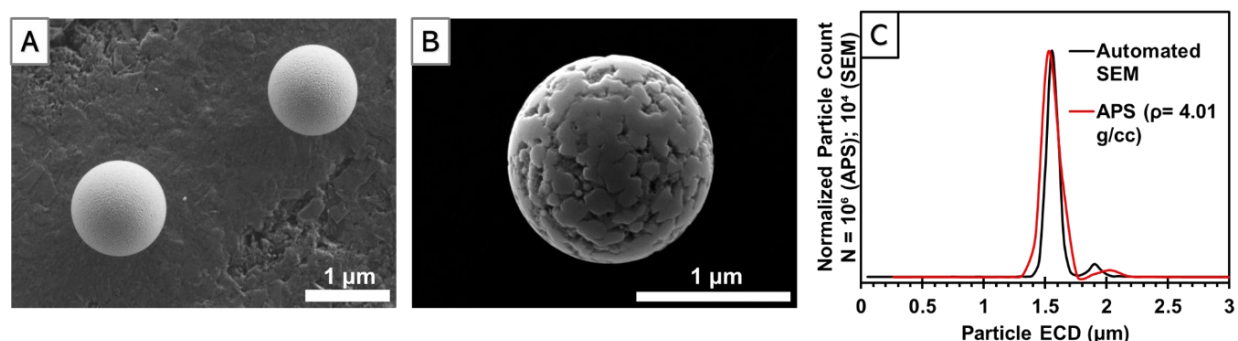


Figure 3. SEM images (A) and (B) of representative WO_3 particles and particle size comparison (C) by APS and APM-SEM consolidation.

Following initial synthesis of μg -scale particle production, effort to demonstrate the feasibility for mg-scale production of E μ P_s was undertaken, involving up to 30 hours of sustained operation of the THESEUS system using similar parameters as developed for planchet production. Particulate oxide materials were collected from the ESP and the theoretical production rates of MoO_3 and WO_3 E μ P_s were calculated as 3.73 and 2.28 mg/h, respectively.

During production, *in situ* APS measurements were collected to assess the stability of particle size and concentration. While this operation involved multi-day particulate batch production, MoO_3 and WO_3 particulates retained their spherical morphology, monodispersity, and relative particle sizes (**Figure 4**). This lab-scale production coupled with the uniformity of particulate size indicates promise for future scale-up.

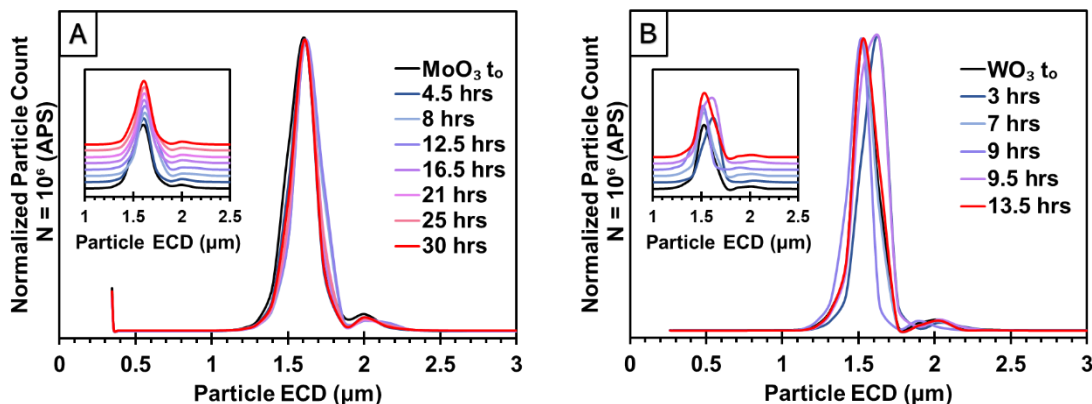


Figure 4. Aerodynamic size for mg-scale production of (A) MoO₃ over 30 hours and (B) WO₃ over 13.5 hours with stacked plot inserted for clarity.

X-ray Diffraction Characterization

Structural and phase characterizations of the MoO₃ and WO₃ particulates were studied using PXRD and Raman spectroscopy. The PXRD patterns of these EμPs are characterized as sharp detectable peaks indicating well-crystallized materials (**Figure 5**).

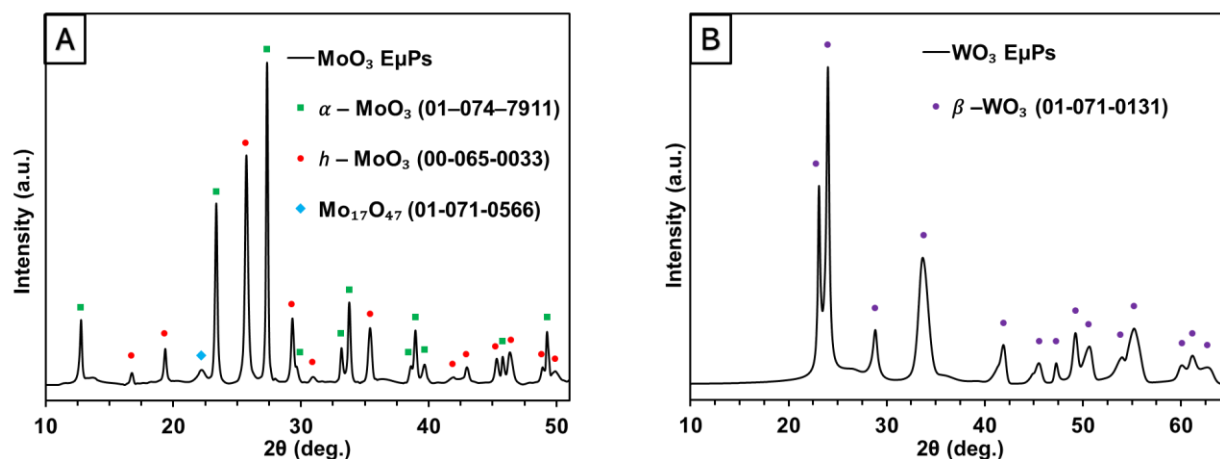


Figure 5. Powder XRD patterns of the synthesized (A) MoO₃ and (B) WO₃ particulates as indexed with their respective phases and corresponding powder diffraction files.

With the operating temperature (700 °C) of the furnace, α -MoO₃ phase should be expected to form. However, the PXRD pattern of molybdenum oxide EμPs indicates a mixture of the orthorhombic α -MoO₃ and hexagonal h -MoO₃ phases as well as a trace hypostoichiometric MoO_{2.76} phase, (**Figure 5**) which are induced by rapid calcination. The formation of α -MoO₃ from h -MoO₃ is known to irreversibly occur above 400 °C.²² Mixed oxide phases (α - and h -MoO₃) and reduced species (Mo₄O₁₁, =MoO_{2.75}) have been previously observed during the production of molybdenum oxide particles using spray pyrolysis techniques as controlled by temperature and Mo feedstock concentration.¹⁴

The dehydration process for tungstic acid (800 °C) exceeded the temperature at which the tetragonal phase (α -WO₃) can form in bulk material, however each of the trioxide phases are formed by corner or edge shared WO₆ octahedral where the higher temperature phases (α -, β -WO₃) often relax toward the more stable and lower density monoclinic phase (γ -WO₃) during cooling to

room temperature.²³ Rather than α - or γ -WO₃ phases, the experimental PXRD pattern (**Figure 5Figure 5B**) indicates the formation of a highly crystalline material whose pattern matches precisely with the orthorhombic (β -WO₃) phase, likely the result of rapid and nonequilibrium cooling.

The crystallinity of the E μ Ps was also investigated using both Scherrer and Williamson-Hall methods²⁴ while considering a shape factor of 1 and X-ray wavelength of 0.15406 nm for Cu K α . The crystallite size of these E μ Ps show relatively good agreement between methods, where MoO₃ crystallite sizes were estimated as 34.54 and 28.09 nm and those for WO₃ were estimated as 16.57 and 9.27 nm via the Scherrer and Williamson-Hall methods, respectively. The discrepancy observed is primarily due to lattice strain not considered in Scherrer formulation, meaning the Williamson-Hall method provides a better approach for the estimation of crystallite size. The increased crystallite size for MoO₃ can likely be attributed to the multiple phases present compared to the single WO₃ phase.

Raman Spectroscopy Characterization

The structures of the MoO₃ and WO₃ particulates were investigated by Raman spectroscopy (**Figure 6Figure 6**) to identify their vibrational properties and phases in relation to their synthetic routes and PXRD characterizations. There were no significant differences observed between Raman spectra from different production campaigns of the same type of E μ P, confirming the homogeneity of the crystal structures.

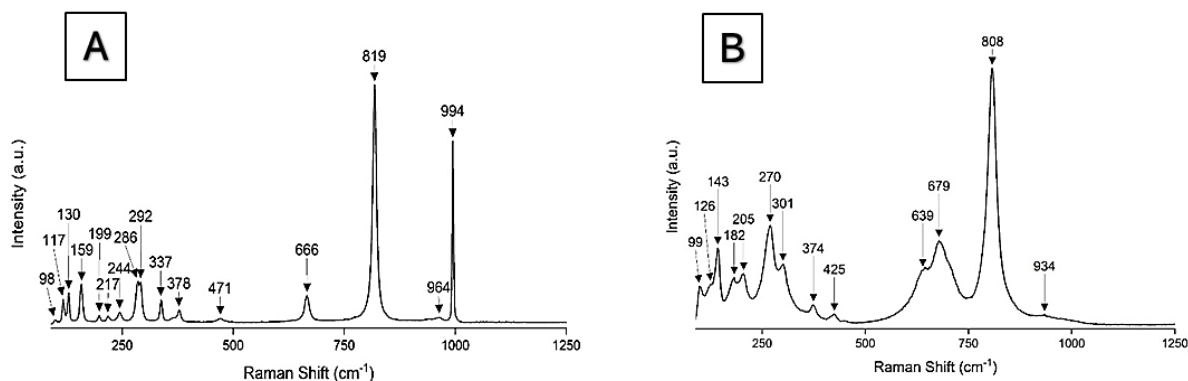


Figure 6. Single particle μ -Raman spectra of (A) MoO₃ and (B) WO₃.

The Raman spectrum of MoO₃ E μ Ps (**Figure 6Figure 6A**) exhibits well-defined Raman bands matching literature values – primarily for high crystalline α -MoO₃ (orthorhombic) materials.²⁵ The Raman bands at 994 cm⁻¹ and 819 cm⁻¹ are assigned to the asymmetric and symmetric stretching frequency of the Mo=O bonds, respectively, whereas the 666 cm⁻¹ band is due to the asymmetric stretching of O–Mo–O. Additional Raman bands due to various lattice modes within the crystalline structure of MoO₃ E μ Ps occur at lower frequency. Of particular interest, the intensity ratio of the wagging modes of MoO₃ (O=Mo=O) as observed at 286 cm⁻¹ and 292 cm⁻¹ reflects a partially distorted structure due to oxygen deficiency.^{26, 27} This observation further supports the experimental PXRD pattern for MoO₃ particulates.

The Raman spectrum of WO₃ E μ Ps (**Figure 6Figure 6B**) also shows vibrational bands reflecting literature, where the bands between 630–810 cm⁻¹ are attributed to either the antisymmetric stretching of W–O–W bonds or the symmetric stretching of O–W–O bonds and the weak (low intensity) band at 934 cm⁻¹ is attributed to the vibration of terminal W=O bonds.^{21, 28, 29} The lower

frequency regions in the spectrum occur due to various lattice modes which are consistent to orthorhombic WO₃ crystalline structure and as confirmed by the experimental PXRD pattern.

Conclusion

Highly uniform metal oxide EμPs with tailorable size were successfully manufactured using the SRNL-developed THESEUS system, with targeted applications including use as taggants within nuclear fuel. Good agreement was achieved between aerodynamic and automated SEM sizing measurements for the generated MoO₃ and WO₃ particles, indicating monodisperse particle populations, with geometric standard deviations (σ_G) below 1.25. This monodispersity indicates a high degree of compositional homogeneity, as evidenced by the results from PXRD and Raman analysis. Phases observed matched the predicted oxides of MoO₃ and WO₃, with MoO₃ presenting with multiple polymorphs and a trace hypostoichiometric phase. This observation of multiple, similar MoO₃ phases with variation in unit cell size is likely the cause of the decreased apparent density and the visible surface porosity. The ability to produce highly homogenous MoO₃ and WO₃ EμPs provides a foundation for the production of isotopically perturbed EμPs and will support ongoing and future investigations towards the application of isotopically-barcoded taggants within the nuclear fuel cycle.

Acknowledgements

This work was produced by Savannah River National Laboratory (Battelle Savannah River Alliance, LLC) under Contracts No. 89303321CEM000080 with the U.S. Department of Energy. This work was conducted as a part of the National Nuclear Security Administration Defense Nuclear Nonproliferation Research and Development (NNSA DNN R&D) Intentional Forensics Venture (LA21-V-IntentionalForensics-NTNF1Bb).

References

1. Paunescu, D.; Stark, W. J.; Grass, R. N., Particles with an identity: tracking and tracing in commodity products. *Powder technology* **2016**, *291*, 344-350.
2. Müssig, S.; Reichstein, J.; Miller, F.; Mandel, K., Colorful Luminescent Magnetic Supraparticles: Expanding the Applicability, Information Capacity, and Security of Micrometer-Scaled Identification Taggants by Dual-Spectral Encoding. *Small* **2022**, *18*, (13), 2107511.
3. Arppe, R.; Sørensen, T. J., Physical unclonable functions generated through chemical methods for anti-counterfeiting. *Nature Reviews Chemistry* **2017**, *1*, (4), 0031.
4. Donohue, D.; Vogt, S.; Ciurapinski, A.; Ruedenauer, F.; Hedberg, M. *Particle analysis of environmental swipe samples*; IAEA-SM-367/10/07: 2001.
5. Keegan, E.; Kristo, M. J.; Toole, K.; Kips, R.; Young, E., Nuclear forensics: scientific analysis supporting law enforcement and nuclear security investigations. In ACS Publications: 2016.
6. Betti, M.; Tamborini, G.; Koch, L., Use of secondary ion mass spectrometry in nuclear forensic analysis for the characterization of plutonium and highly enriched uranium particles. *Analytical Chemistry* **1999**, *71*, (14), 2616-2622.
7. LaMont, S.; Phillips, J.; Bedell, J.; Goorevich, R.; Nusbaum, D.; Karpas, Z.; Maimon, E.; Sadan, Y.; Reich, G. In *Use of chemical and isotopic tracers as part of an improved safeguards approach in uranium conversion facilities*, 8th International Conference on Facility Operations: Safeguards Interface 2008, 2008; 2008; pp 111-130.

8. Wilson, B.; Shields, A.; Russell, N.; Nelson, A.; Ulrich, T.; Scott, S.; Wellons, M. *Irradiation of Isotopically Tagged UO₂ Fuel for Intentional Forensics Purposes*; Oak Ridge National Lab.(ORNL), Oak Ridge, TN (United States): 2022.
9. Kristo, M.; Robel, M.; Hutcheon, I. *Nuclear Forensics and Attribution for Improved Energy Security: The Use of Taggants in Nuclear Fuel*; Lawrence Livermore National Lab.(LLNL), Livermore, CA (United States): 2007.
10. Messing, G. L.; Zhang, S. C.; Jayanthi, G. V., Ceramic powder synthesis by spray pyrolysis. *Journal of the American Ceramic Society* **1993**, 76, (11), 2707-2726.
11. Govender, M.; Shikwambana, L.; Mwakikunga, B. W.; Sideras-Haddad, E.; Erasmus, R. M.; Forbes, A., Formation of tungsten oxide nanostructures by laser pyrolysis: stars, fibres and spheres. *Nanoscale Research Letters* **2011**, 6, (1), 166.
12. Nakakura, S.; Arif, A. F.; Rinaldi, F. G.; Hirano, T.; Tanabe, E.; Balgis, R.; Ogi, T., Direct synthesis of highly crystalline single-phase hexagonal tungsten oxide nanorods by spray pyrolysis. *Advanced Powder Technology* **2019**, 30, (1), 6-12.
13. Nandiyanto, A. B. D.; Arutanti, O.; Ogi, T.; Iskandar, F.; Kim, T. O.; Okuyama, K., Synthesis of spherical macroporous WO₃ particles and their high photocatalytic performance. *Chemical Engineering Science* **2013**, 101, 523-532.
14. Choi, H.; Kim, D.; Yoon, S. P.; Han, J.; Ha, S.; Kim, J., Production of molybdenum oxide particles with high yield by ultrasonic spray pyrolysis and their catalytic activity toward partial oxidation of n-dodecane. *Journal of Analytical and Applied Pyrolysis* **2015**, 112, 276-283.
15. Ding, Q. P.; Huang, H. B.; Duan, J. H.; Gong, J. F.; Yang, S. G.; Zhao, X. N.; Du, Y. W., Molybdenum trioxide nanostructures prepared by thermal oxidization of molybdenum. *Journal of Crystal Growth* **2006**, 294, (2), 304-308.
16. Kumar, V.; Wang, X.; Lee, P. S., Formation of hexagonal-molybdenum trioxide (h-MoO₃) nanostructures and their pseudocapacitive behavior. *Nanoscale* **2015**, 7, (27), 11777-86.
17. Scott, S. M.; Baldwin, A. T.; Bronikowski, M. G.; II, M. A. D.; Inabinet, L. A.; Kuhne, W. W.; Naes, B. E.; Smith, R. J.; Eliel, V.-A.; Tenner, T. J.; Wurth, K. N.; Wellons, M. S., Scale-up And Production Of Uranium-bearing QC Reference Particulates By An Aerosol Synthesis Method. *Proceedings of the Joint INMM & ESARDA 2021 Meeting* **2021**.
18. Benjamin E. Naes, S. S., Abigail Waldron, Seth Lawson, Michael G. Bronikowski, Laken A. Inabinet, Ross J. Smith, Kimberly N. Wurth, Travis J. Tenner and Matthew Wellons, Production of Mixed Element Actinide Reference Particulates to Support Nuclear Safeguards using THESEUS, an Aerosol-based Particulate Synthetic Methodology. *Under Review* **2023**.
19. Carlson, D. C.; Degange, J. J.; Cable-Dunlap, P., Portable aerosol contaminant extractor. In Google Patents: 2005.
20. Leisegang, T.; Levin, A.; Walter, J.; Meyer, D., In situ X-ray analysis of MoO₃ reduction. *Crystal Research and Technology: Journal of Experimental and Industrial Crystallography* **2005**, 40, (1-2), 95-105.
21. Salje, E., The orthorhombic phase of WO₃. *Acta Crystallographica Section B* **1977**, 33, (2), 574-577.
22. Ramana, C. V.; Atuchin, V. V.; Troitskaia, I. B.; Gromilov, S. A.; Kostrovsky, V. G.; Saupe, G. B., Low-temperature synthesis of morphology controlled metastable hexagonal molybdenum trioxide (MoO₃). *Solid State Communications* **2009**, 149, (1), 6-9.
23. Zheng, H.; Ou, J. Z.; Strano, M. S.; Kaner, R. B.; Mitchell, A.; Kalantar-zadeh, K., Nanostructured tungsten oxide—properties, synthesis, and applications. *Advanced Functional Materials* **2011**, 21, (12), 2175-2196.

24. Cullity, B. D.; Stock, S. R., *Elements of X-ray Diffraction*. 3rd ed.; Pearson New International Edition: 2001.
25. Silveira, J. V.; Vieira, L. L.; Filho, J. M.; Sampaio, A. J.; Alves, O. L.; Souza Filho, A. G., Temperature-dependent Raman spectroscopy study in MoO₃ nanoribbons. *Journal of Raman spectroscopy* **2012**, *43*, (10), 1407-1412.
26. Dieterle, M.; Weinberg, G.; Mestl, G., Raman spectroscopy of molybdenum oxides Part I. Structural characterization of oxygen defects in MoO_{3-x} by DR UV/VIS, Raman spectroscopy and X-ray diffraction. *Physical Chemistry Chemical Physics* **2002**, *4*, (5), 812-821.
27. Mestl, G.; Srinivasan, T.; Knözinger, H., Mechanically activated MoO₃. 3. Characterization by vibrational spectroscopy. *Langmuir* **1995**, *11*, (10), 3795-3804.
28. Daniel, M. F.; Desbat, B.; Lassegues, J. C.; Gerand, B.; Figlarz, M., Infrared and Raman study of WO₃ tungsten trioxides and WO₃·xH₂O tungsten trioxide hydrates. *Journal of Solid State Chemistry* **1987**, *67*, (2), 235-247.
29. Gabrusenoks, J.; Veispals, A.; Czarnowski, A. v.; Meiwes-Broer, K. H., Infrared and Raman spectroscopy of WO₃ and CdWO₄. *Electrochimica Acta* **2001**, *46*, 2229-2231.