

Synthesis of Metal Hydrides by Mechanical Alloying in an Attritor Mill: FY07 Status Report (U)

K.M. Fox

October 2007

Materials Science and Technology
Savannah River National Laboratory
Aiken, SC 29808

Prepared for the U.S. Department of Energy Under
Contract Number DEAC09-96SR18500



DISCLAIMER

This report was prepared by Washington Savannah River Company (WSRC) for the United States Department of Energy under Contract No. DE-AC09-96SR18500 and is an account of work performed under that contract. Neither the United States Department of Energy, nor WSRC, nor any of their employees makes any warranty, expressed or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness, of any information, apparatus, or product or process disclosed herein or represents that its use will not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trademark, name, manufacturer or otherwise does not necessarily constitute or imply endorsement, recommendation, or favoring of same by WSRC or by the United States Government or any agency thereof. The views and opinions of the authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

Printed in the United States of America

**Prepared For
U.S. Department of Energy**

The Savannah River National Laboratory is operated for the U.S. Department of Energy by Washington Savannah River Company.

Keywords: *Metal hydrides,
Mechanical alloying, Attritor milling*

Retention: *permanent*

Synthesis of Metal Hydrides by Mechanical Alloying in an Attritor Mill: FY07 Status Report (U)

K.M. Fox

October 2007

Materials Science and Technology
Savannah River National Laboratory
Aiken, SC 29808

Prepared for the U.S. Department of Energy Under
Contract Number DEAC09-96SR18500



REVIEWS AND APPROVALS

AUTHOR:

K.M. Fox, Process Science and Engineering

Date

TECHNICAL REVIEWER:

D.J. Hathcock, Materials Science and Technology

Date

APPROVERS:

N.C. Iyer, Manager, Materials Science and Technology

Date

G.T. Chandler, Manager, Materials Performance and Corrosion Technology

Date

D.A. Crowley, Manager, Stabilization Science Research

Date

R.L. Rabun, Defense Projects Engineering
PDRD Program Manager

Date

EXECUTIVE SUMMARY

The objective of this task was to demonstrate that metal hydrides could be produced by mechanical alloying in the quantities needed to support the tritium production facilities at the Savannah River Site. The objective for the FY07 portion of this task was to demonstrate the production of Zr-Fe getter materials by mechanical alloying and begin to optimize the milling parameters.

Three starting compositions (ratios of elemental Zr and Fe powders) were selected and attritor milled under argon for times of 8 to 60 hours. Hexane and liquid nitrogen were used as process control agents. In general, milling times of at least 24 hours were required to form the desired Zr_2Fe and Zr_3Fe phases, although a considerable amount of unalloyed Zr and Fe remained. Milling in liquid nitrogen does not appear to provide any advantages over milling in hexane, particularly due to the formation of ZrN after longer milling times.

Carbides of Zr formed during some of the milling experiments in hexane. Formation of carbides during milling appears to be much less of an issue than formation of nitrides, although some of the phases that were not able to be identified in the XRD results may also be carbides. Additional XRD experiments should be designed to improve signal to noise ratio (i.e., longer count times) and use a wider scan range to better identify phases that were not clear in the original data.

Elemental Zr was present in the as-milled material but not detected after annealing for milling times of 48 and 60 hours. It may be that after intimate mixing of the powders in the attritor mill the annealing temperature was sufficient to allow for the formation of a Zr-Fe alloy. The phase diagram for the binary Zr-Fe system agrees with this proposition. If this is the case, then the annealing conditions should also be investigated and optimized to form as much of the Zr-Fe alloy as possible in the milled powder. Also, this finding would mean that milling times of more than 48 hours are not necessary. Further investigation of this conversion is necessary, and could provide an opportunity for reducing the amount of unreacted metal powder after milling.

Elemental Fe remained in all of the powders after annealing for all of the milling times tested. This may indicate that the ratio of Zr to Fe needs to be increased in order to improve the yield of the desired Zr-Fe alloys.

Particle size analysis data are presented to aid in the selection of filters for future hydrogen sorption testing. Based on the XRD results, four samples were suggested for further XRD analysis and hydrogen sorption testing:

- Zr_2Fe , 24 hr milling, annealed
- Zr_2Fe , 24 hr milling in LN_2 , annealed
- Zr_3Fe , 24 hr milling, annealed
- Zr_3Fe , 48 hr milling, annealed

These four samples showed the largest volume (based on relative peak intensities) of the desired Zr_2Fe and Zr_3Fe alloys.

This page intentionally left blank.

TABLE OF CONTENTS

List of Tables	viii
List of Figures	ix
List of Abbreviations	x
1.0 Introduction	1
1.1 Zirconium – Iron Alloys	1
1.2 Mechanical Alloying.....	2
1.3 Attrition Milling.....	2
1.4 Mechanical Alloying of Metal Hydrides	4
2.0 Experimental Procedure	5
3.0 Results and Discussion	6
3.1 XRD Results	7
3.2 Particle Size Analyses.....	9
4.0 Conclusions and Recommendations	12
5.0 Acknowledgements	14
6.0 References	16
Appendix A	19

LIST OF TABLES

Table 3-1. Summary of XRD results for the milled powders.....	9
---	---

LIST OF FIGURES

Figure 1-1. Schematic drawing of a high-speed attritor. ¹¹	2
Figure 1-2. Diagram of media collisions with agitator arm and milled particles. ¹¹	3
Figure 3-1. Particle size analysis results for the Zr ₂ Fe mixture mechanically alloyed in LN ₂ and sampled at four intervals.	10
Figure 3-2. Particle size analysis results for the mechanically alloyed Zr ₂ Fe mixture sampled at four intervals.	10
Figure 3-3. Particle size analysis results for the mechanically alloyed Zr _{2.5} Fe mixture sampled at four intervals.	11
Figure 3-4. Particle size analysis results for the mechanically alloyed Zr ₃ Fe mixture sampled at four intervals.	11

LIST OF ABBREVIATIONS

DOE	Department of Energy
IMP	Institute of Materials Processing
LN ₂	Liquid Nitrogen
NNSA	National Nuclear Security Administration
PCA	Process Control Agent
SRNL	Savannah River National Laboratory
SRS	Savannah River Site
WSRC	Washington Savannah River Company
XRD	X-ray Diffraction

1.0 Introduction

The objective of this task was to demonstrate that metal hydrides could be produced by mechanical alloying in the quantities needed to support the tritium production facilities at the Savannah River Site. The objective for the FY07 portion of this task was to demonstrate the production of Zr-Fe getter materials by mechanical alloying and begin to optimize the milling parameters.

1.1 Zirconium – Iron Alloys

Zr-Fe alloys are used as getters for hydrogen and its isotopes, including tritium. Metal alloy getters are preferred in applications where operation in a nitrogen atmosphere is necessary, and where catalytic oxidation of the isotopes would produce unwanted (and highly toxic) tritiated water. Tritium gettering in Zr-Fe alloys arises through dissolution of atomic tritium in the alloy, which has a low tritium equilibrium partial pressure.¹

A commercially available Zr-Fe alloy, SAES ST198, is currently in use in the tritium facilities at the Savannah River Site. The chemical composition of ST198 has been reported as 76.5 wt % Zr, 23.5 wt % Fe,² and 73.6 wt % Zr, 23.3 wt % Fe,³ both of which correspond to Zr_2Fe . ST198 has relatively low reactivity with nitrogen,^{1,3,4} making it quite useful for removal of hydrogen isotopes in a nitrogen gas stream. Zr_2Fe has been shown to remain an effective getter material for hydrogen isotopes even as the nitrogen concentration within the alloy becomes significant.⁵ However, purification factors decrease as nitrogen concentration increases, necessitating increased residence times for optimal efficiency.⁵ Hydrogen absorption by ST198 is inhibited by Q_2O , CQ_4 and NQ_3 (where Q is any hydrogen isotope) impurities in the gas stream.⁶ ST198 also has a high affinity for oxygen, which depletes its gettering capacity for hydrogen isotopes.¹ Typically a ZrMnFe getter, such as the SAES ST909, is used to remove these impurities from the gas stream before it reaches the ST198 getter. ST909 will crack various impurities and retains carbon, nitrogen and oxygen, but very little of the hydrogen isotopes.⁶

Several authors have investigated the phases present in ST198 and the stability of these phases after thermal cycling in the presence of hydrogen.^{3,4} ST198 consists mainly of Zr_2Fe , with other minor phases including Zr_5FeSn , $ZrFe_2$, α -Zr and Zr_6FeO .³ It is not clear whether the tin-containing phase exists as an impurity or is included intentionally, and difficulty in detecting it via XRD may indicate that it is amorphous.³ The oxide phase is likely present due to oxygen contamination of the material.³ Zr_2Fe is considered to be a supercooled or metastable phase, and has been shown to convert to the equilibrium Zr_3Fe phase above 600 °C.^{3,4} Coleman et al. provide a summary of crystal structure determinations for Zr_2Fe and Zr_3Fe alloys: Zr_2Fe is body centered tetragonal ($I4/mcm$) and Zr_3Fe is orthorhombic ($Cmcm$).⁴ Hydrides of the Zr_2Fe phase have been shown to be stable at higher temperatures (disproportionation beginning at 400 °C) than those of Zr_3Fe (disproportionation beginning at 200-300 °C).⁴ Hydrides of both phases dissociate upon further heating to ZrH_x , α -Fe and $ZrFe_2$.^{3,4}

While the properties and performance of the ST198 material have been well characterized, the method of commercial production is not known. Small quantities of the alloy are typically produced for research purposes by arc melting or melt spinning,^{7,8} although these techniques are not necessarily economical for production on the scale necessary to support the tritium facilities at the Savannah River Site (SRS). A production method that can be performed in-house or by a domestic subcontractor to produce Zr_2Fe alloys at reasonable cost and in quantities necessary to support the SRS tritium facilities is desirable.

1.2 Mechanical Alloying

Mechanical alloying is the process of cold welding, fracturing and rewelding of powder particles in a high-energy mill.⁹ This technique can be used to synthesize a variety of metal alloys, as well as metastable phases, currently of interest for use as catalysts and hydrogen storage materials.⁹ Mechanical alloying is uniquely suited for the production of metastable phases since, as it is a solid-state processing technique, the thermodynamic and kinetic limitations imposed on other processing methods do not necessarily apply.

Several different types of mechanical mills can be used. The choice of mill is dependent largely on the amount of material to be produced. The components of the alloy are added to the mill vessel along with the milling media and, in most cases, a small amount of a lubricant such as stearic acid. The mill is then operated at high-speed for periods of minutes to hours.

1.3 Attrition Milling

The attritor, also referred to as a stirred ball mill,¹⁰ is a high speed mill used for rapid particle size reduction. Attritors have been developed for both wet and dry grinding applications, and are available in batch and continuous loading configurations. The attritor uses a stationary vessel charged with grinding media and the material to be milled. The mill charge is agitated by a motor driven shaft with horizontal arms (see Figure 1-1).

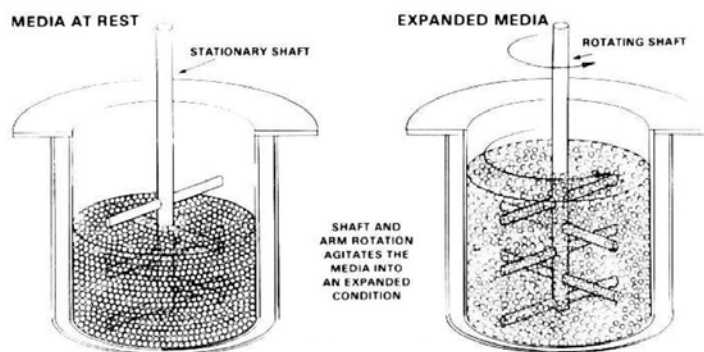


Figure 1-1. Schematic drawing of a high-speed attritor.¹¹

The shaft is rotated at a fairly high speed, which produces high tip velocities at the ends of the agitator arms. This imparts a large amount of energy directly to the milling media (see Figure 1-2).

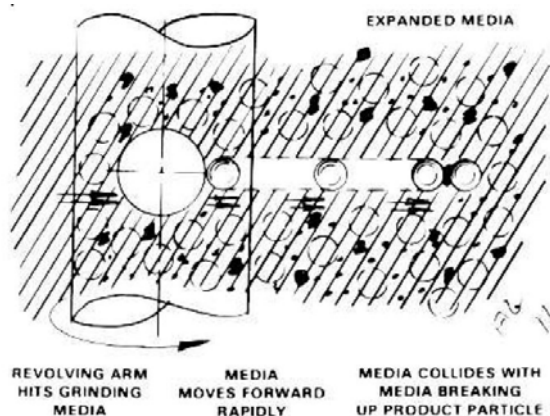


Figure 1-2. Diagram of media collisions with agitator arm and milled particles.¹¹

Size reduction is achieved by impact and shearing forces as the milling media collide with one another. The motion of the agitator arms produces a region of high media turbulence that is at approximately two thirds of the radius from the central shaft.¹⁰ This results in little wear occurring on the vessels walls. Contamination from the vessel walls is therefore reduced, and thinner walls can be used to promote heat transfer and improve temperature control during the milling operation.¹⁰

The size and composition of the milling media used in an attritor has a major impact on its operation.¹⁰ Media used for attrition milling are typically spherical with a diameter of 3-4 mm. Proper selection of media size depends on the size of the initial feed and the intended final particle size. Larger media must be used to grind larger feed material, but smaller media are more effective at fine grinding. The type of material used for the grinding media depends on several factors. When contamination is a concern, materials that are compatible with the feed should be used for both the milling media and the milling vessel. The media should be denser than the feed to prevent floating in the vessel, and harder than the feed to reduce wear. Higher density milling media can greatly reduce milling times.

Batch-type attritors are utilized for dry grinding, particularly when the feed powders must be milled under a protective atmosphere. Material is charged directly into the top of the vessel, can be sampled at any point during the milling process, and additions can be made to the charge without stopping the mill.¹⁰ The vessel can be charged and sealed in an inert glove box prior to milling, or the entire attritor can be contained within a glove box.

In addition to size reduction, the considerable amount of energy imparted to the feed material by an attritor can be used for mechanical alloying of metal particles. The increase in milling energy is due primarily to an increase in the number of media collisions, as evidenced in experiments involving the stress-induced transformation of partially-stabilized zirconia powders.¹²

An important aspect of this work was to develop a process that could be used to produce the quantities of materials necessary to satisfy the needs of the tritium facilities. Attritor mills are commercially available with capacities many times larger than that used in the tests that are detailed in this report. Therefore, the processes developed with a research-scale attritor could be scaled-up by using larger mills. Preferably, the milling vessel would be housed in an inert glove box with the shaft magnetically coupled to the drive mechanism through the wall of the glove box.

This would eliminate the need to load the vessel in the glove box and then transfer the vessel out to the mill.

1.4 Mechanical Alloying of Metal Hydrides

Several technical reports and patents concerning the science of mechanical alloying^{9, 13} and, more specifically, fabrication of Zr-Fe alloys by mechanical alloying^{7, 14-16} were reviewed prior to initiating this experimental program:

Hellstern and Schultz reported on mechanical alloying Fe-Zr materials, showing that milling of the elemental metal powders will produce alloys with amorphous structures.¹⁵ They also noted a transformation of α -Zr to the high pressure ω -Zr phase after milling of a Fe₂₀Zr₈₀ material.¹⁴

Biegel et al. compared the crystallization behavior of amorphous Fe₃₀Zr₇₀ alloys prepared by melt spinning and mechanical alloying.⁷ The melt spun material crystallized as α -Zr, ω -Zr and Zr₂Fe at moderate temperatures, which then converted to Zr₃Fe above 400 °C. They report that the mechanically alloyed powder crystallized directly to the Zr₃Fe,⁷ although other phases appear to be present in the X-ray diffraction spectra that they present.

Pilar et al. investigated the use of various process control agents (PCA) in controlling the amount of cold welding and fracturing that occurs during the mechanical alloying process for FeNiZrB alloys (of interest for their soft magnetic properties).¹⁶ Milling was completed in a planetary ball mill under argon atmosphere. The results showed that powders milled with hexane and naphthalene formed a more disordered structure with very small crystallite sizes (4 nm) as compared to other organics and powders milled without a PCA. The powders milled in hexane and naphthalene also had better thermal stability after annealing at 450 °C and reduced amounts of oxygen contamination as compared to the other organics, although a significant amount of carbon (>1.8 at %) remained in the milled powder.

Based the literature review, mechanical alloying appears to be a possible route for the fabrication of Zr-Fe alloys for use as getter materials. Heat treatment will likely be necessary to evolve the desired phases after the milling process is completed. The literature provides no clear direction as to the optimum starting composition (ratio of elemental Zr and Fe powders) or the optimum milling conditions. These variables will be investigated as part of this study.

2.0 Experimental Procedure

Mechanical alloying experiments were carried out at the Institute for Materials Processing (IMP) at Michigan Technological University. IMP has a large argon glove box facility containing a research-scale attritor mill, an annealing furnace and various powder handling equipment. This allowed all aspects of the mechanical alloying work to be performed under a protective argon atmosphere. Samples were removed only for composition and particle size characterization, as described later.

Elemental Zr and Fe metal powders were used as the starting materials for these experiments. Both powders had an initial particle size of -325 mesh and a purity of better than 99%. The attritor mill vessel and agitator were stainless steel. Cylindrical, through-hardened carbon steel (SAE 1065) milling media with converse hemispherical ends were used. The mill was operated at 650 RPM with chilled kerosene ($< 0^{\circ}\text{C}$) cooling.

Three starting compositions were used in these experiments due to the uncertainty in the optimum stoichiometry for application to hydrogen gettering. The elemental Zr and Fe metal powders were added to the mill in mass ratios corresponding to Zr_2Fe , $\text{Zr}_{2.5}\text{Fe}$ and Zr_3Fe . Stearic acid was added at 1 wt % as a lubricant. The milled powder was sampled after milling for 8, 24, 48 and 60 hours. The samples were collected and stored under argon. In addition, a second milling run with the Zr_2Fe composition was performed with liquid nitrogen (LN_2) charged to the milling vessel and sampled at the same intervals. These experiments produced a total of 16 powder samples for characterization.

Upon milling the first composition, Zr_2Fe without LN_2 , caking of the powder was noted after 8 hours. The powder partially adhered to the grinding media after 24 hours of milling, and completely coated the vessel wall and grinding media after 48 hours of milling. The process was changed to wet grinding with hexane to overcome this problem. The ratio of powder to milling media to hexane was 1:5:0.5 by volume. After completion of the milling cycle, the hexane was evaporated under vacuum in the oven attached to the glove box, then backfilled with argon for sampling. The powder from the milling run where caking occurred was discarded, and the experiment was re-run using hexane.

Each of the 16 specimens was analyzed by X-ray diffraction (XRD) after milling to identify the crystalline phases present. Loose powder samples of each of the 16 specimens were annealed in argon at 600°C for 1 hour, since amorphization of the powder was expected after milling. Samples of each of the annealed powders were also analyzed by XRD to determine whether a reduction in amorphization occurred, and if so, to identify the crystalline phases that resulted.

The particle size distribution of each of the milled powder samples (prior to annealing) was measured using a laser light diffraction particle size analyzer. Stainless steel specimen containers with copper gaskets were supplied by SRNL for return of specimens from the subcontractor.

This page intentionally left blank.

3.0 Results and Discussion

3.1 XRD Results

Each of the milled powder samples was examined by XRD both before and after annealing. The XRD results for each sample are given in detail in Appendix A. A summary of these data is provided in Table 3-1.

After 8 hours of milling, all of the milled powders consisted of unreacted Zr and Fe. Broadening of the XRD peaks was observed for all of the samples, which is indicative of a reduction in average crystallite size. After annealing, the powders milled for 8 hours consisted mainly of unreacted Zr and Fe. ZrC was identified in the Zr₂Fe composition. The Zr₂Fe in LN₂ and Zr_{2.5}Fe compositions contained some Zr₃Fe, while the Zr₃Fe composition contained some Zr₄Fe. A small amount of Fe₂O₃ was identified in the Zr₂Fe and Zr₂Fe in LN₂ compositions. It is unlikely that this oxygen was picked up from the atmosphere since the partial pressure of oxygen was maintained to a very low value in the glove box. The Fe₂O₃ may instead be the result of contamination from the steel attritor mill components and media, which had previously been exposed to air.

All of the starting compositions contained unreacted Zr and Fe after 24 hours of milling. Upon annealing of the powders milled for 24 hours, Zr₃Fe (Zr₂Fe for the powders milled in LN₂) crystallized, along with the unreacted Zr and Fe.

After 48 hours of milling, the powders generally remained unreacted Zr and Fe, with the possible inclusion of a small amount of Zr₄Fe. Amorphization was apparent in the Zr₂Fe composition milled in LN₂ and the Zr₃Fe composition. After annealing, the Zr₂Fe, Zr_{2.5}Fe and Zr₃Fe compositions contained Zr₂Fe, unreacted Fe, possible ZrFe₂ and a series of peaks that were not matched to any phase in the database (labeled 'unidentified phase' in Table 3-1). The Zr₂Fe composition milled in LN₂ crystallized to mainly ZrN after annealing. Iron-rich Zr-Fe phases and unreacted Fe were also present.

All of the powders milled for 60 hours continued to contain unreacted Zr and Fe. Amorphization of the powders is suggested by the broad hump present in all of the 60 hour XRD spectra. An unidentified phase was also present in the Zr₂Fe, Zr_{2.5}Fe and Zr₃Fe compositions. After annealing, the Zr₂Fe, Zr_{2.5}Fe and Zr₃Fe compositions all contained Zr₂Fe, ZrFe₂, unreacted Fe and an unidentified phase. The Zr₂Fe composition milled in LN₂ again crystallized to mainly ZrN after annealing. Iron-rich Zr-Fe phases and unreacted Fe were also present, as well as an unidentified phase.

It is unusual to note that for all the powders milled for 48 or 60 hours, Zr was present in the as-milled material but not detected after annealing. It may be that after intimate mixing of the powders in the attritor mill, the annealing temperature of 600 °C was high enough to allow for the formation of a Zr-Fe alloy. The phase diagram for the binary Zr-Fe system indicates that Zr₃Fe should be stable at the annealing temperature (600 °C).¹⁷ Further investigation of this conversion is necessary, and could provide an opportunity for reducing the amount of unreacted metal powder after milling. In addition, unreacted Fe remained in all of the powders after annealing for all of the milling times tested. This may indicate that the ratio of Zr to Fe needs to be increased in order to improve the yield of the desired Zr-Fe alloys.

Based on these XRD results, four samples are suggested for further XRD analysis and hydrogen sorption testing. These four samples show the largest volume (based on relative peak intensities) of the desired Zr_2Fe and Zr_3Fe alloys:

- Zr_2Fe , 24 hr milling, annealed
- Zr_2Fe , 24 hr milling in LN_2 , annealed
- Zr_3Fe , 24 hr milling, annealed
- Zr_3Fe , 48 hr milling, annealed

Table 3-1. Summary of XRD results for the milled powders.

Composition	Milling Time (hr)	Heat Treatment	XRD Results
Zr ₂ Fe	8	as milled	peak broadening, unreacted Zr and Fe
		600 °C, 1 hour	unreacted Zr and Fe, ZrC, Fe ₂ O ₃
	24	as milled	largely unreacted Zr and Fe
		600 °C, 1 hour	Zr ₃ Fe, some unreacted Zr and Fe
	48	as milled	largely unreacted Zr and Fe, possible Zr ₄ Fe
		600 °C, 1 hour	Zr ₂ Fe, unreacted Fe, and unidentified phase
	60	as milled	amorphization, unreacted Zr and Fe, unidentified phase
		600 °C, 1 hour	amorphization, Zr ₂ Fe, ZrFe ₂ , unreacted Fe, unidentified phase
Zr ₂ Fe in LN ₂	8	as milled	peak broadening, unreacted Zr and Fe
		600 °C, 1 hour	unreacted Zr and Fe, Zr ₃ Fe, possible Fe ₂ O ₃
	24	as milled	unreacted Zr and Fe, possible Zr ₄ Fe
		600 °C, 1 hour	Zr ₂ Fe, unreacted Zr and Fe
	48	as milled	amorphization, unreacted Zr and Fe, possible Zr ₄ Fe
		600 °C, 1 hour	crystallized ZrN, ZrFe ₂ , Zr ₆ Fe ₂₃ , unreacted Fe
	60	as milled	amorphization, possible Zr ₃ Fe, unreacted Zr and Fe
		600 °C, 1 hour	crystallized ZrN, possible Zr ₆ Fe ₂₃ , unreacted Fe, unidentified phase
Zr _{2.5} Fe	8	as milled	peak broadening, unreacted Zr and Fe
		600 °C, 1 hour	unreacted Zr and Fe, Zr ₃ Fe
	24	as milled	unreacted Zr and Fe, possible Zr ₄ Fe
		600 °C, 1 hour	unreacted Zr and Fe, Zr ₃ Fe, ZrC, Fe ₂ O ₃
	48	as milled	unreacted Zr and Fe, possible Zr ₄ Fe
		600 °C, 1 hour	Zr ₂ Fe, ZrFe ₂ , unreacted Fe, unidentified phase
	60	as milled	amorphization, unreacted Zr and Fe, unidentified phase
		600 °C, 1 hour	Zr ₂ Fe, ZrFe ₂ , unreacted Fe, unidentified phase
Zr ₃ Fe	8	as milled	peak broadening, unreacted Zr and Fe
		600 °C, 1 hour	unreacted Zr and Fe, Zr ₄ Fe
	24	as milled	unreacted Zr and Fe, possible Zr ₄ Fe
		600 °C, 1 hour	Zr ₃ Fe, unreacted Zr and Fe
	48	as milled	amorphization, Zr ₄ Fe, unreacted Zr and Fe
		600 °C, 1 hour	Zr ₂ Fe, possible ZrFe ₂ , unreacted Fe, unidentified phase
	60	as milled	amorphization, unreacted Zr and Fe, unidentified phase
		600 °C, 1 hour	Zr ₂ Fe, ZrFe ₂ , unreacted Fe, unidentified phase

3.2 Particle Size Analyses

Figures 3-1 through 3-4 display the results of the particle size analyses for each of the four milling runs. An analysis was performed at each sampling interval. In general, the results show

that as milling time is increased, the particle size distribution becomes broader and shifts to a smaller average size. This is not surprising, as longer milling times provide the time and energy input necessary to further fracture the powder particles. No effort was made to de-agglomerate or control the surface chemistry of the powders. Therefore it is likely that these measurements represent the size of agglomerates in the powders, while the actual crystallite size is considerably smaller. These data are intended to guide the selection of filter sizes for future hydrogen sorption testing, rather than determine the actual particle size.

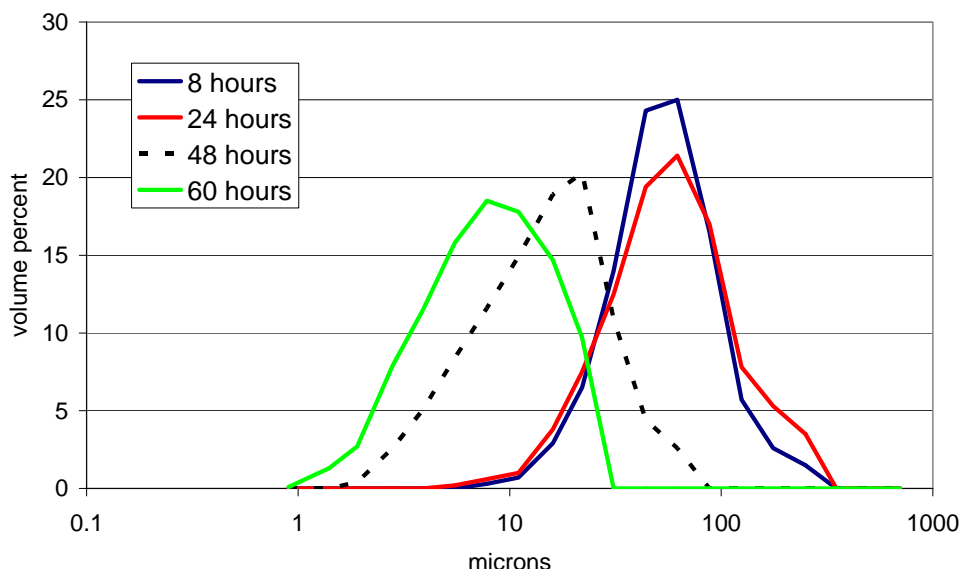


Figure 3-1. Particle size analysis results for the Zr_2Fe mixture mechanically alloyed in LN_2 and sampled at four intervals.

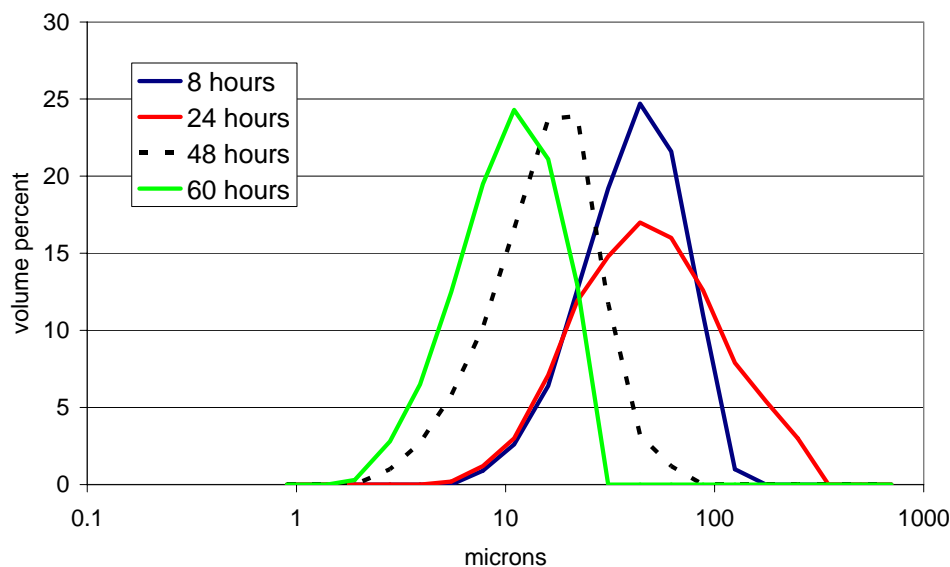


Figure 3-2. Particle size analysis results for the mechanically alloyed Zr_2Fe mixture sampled at four intervals.

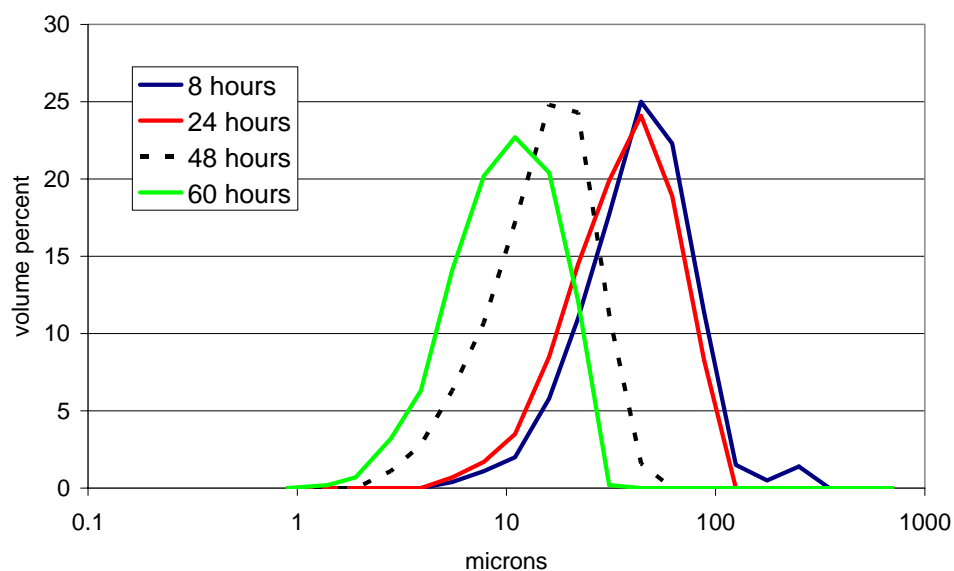


Figure 3-3. Particle size analysis results for the mechanically alloyed $Zr_{2.5}Fe$ mixture sampled at four intervals.

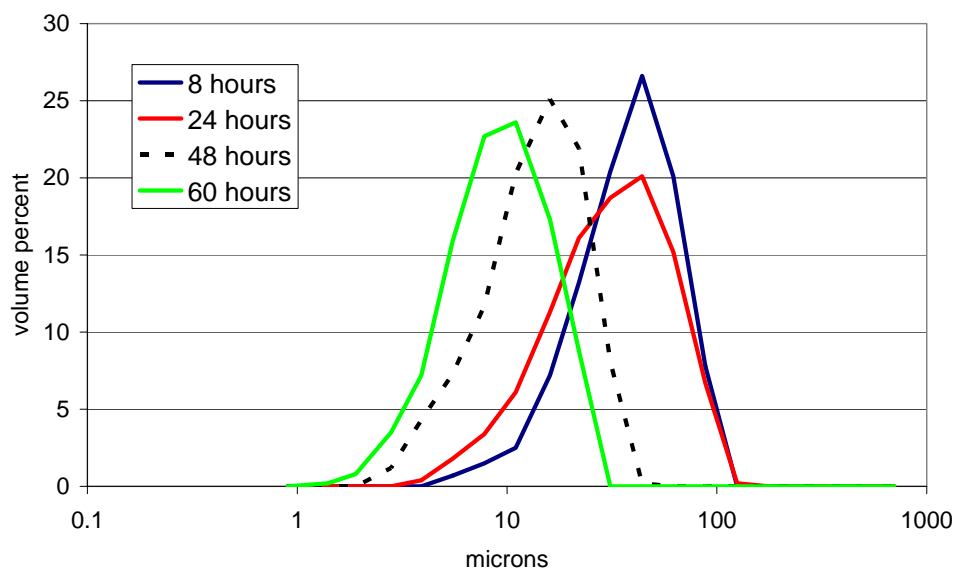


Figure 3-4. Particle size analysis results for the mechanically alloyed Zr_3Fe mixture sampled at four intervals.

This page intentionally left blank.

4.0 Conclusions and Recommendations

In general, milling times of at least 24 hours were required to form the desired Zr_2Fe and Zr_3Fe phases, although a considerable amount of unalloyed Zr and Fe remained before annealing. Milling in LN_2 does not appear to provide any advantages over milling in hexane, particularly due to the formation of ZrN after longer milling times.

Carbides of Zr formed during some of the milling experiments in hexane. While ZrC was identified in only two of the milled powders, further XRD analysis may show that some of the unidentified peaks belong to carbide phases. Formation of carbides during milling appears to be much less of an issue than formation of nitrides (i.e., a much smaller fraction of the Zr powder appears to form carbides, leaving more Zr for the formation of Zr-Fe alloys). Additional XRD experiments should be designed to improve signal to noise ratio (i.e., longer count times) and use a wider scan range to better identify phases that were not clear in the original data.

Elemental Zr was present in the as-milled material but not detected after annealing for milling times of 48 and 60 hours. It may be that after intimate mixing of the powders in the attritor mill the annealing temperature was sufficient to allow for the formation of a Zr-Fe alloy. The phase diagram for the binary Zr-Fe system agrees with this proposition. If this is the case, then the annealing conditions should also be investigated and optimized to form as much of the Zr-Fe alloy as possible in the milled powder. Also, this finding would mean that milling times of more than 48 hours are not necessary. Further investigation of this conversion is necessary, and could provide an opportunity for reducing the amount of unreacted metal powder after milling.

Elemental Fe remained in all of the powders after annealing for all of the milling times tested. This may indicate that the ratio of Zr to Fe needs to be increased in order to improve the yield of the desired Zr-Fe alloys.

Based on the XRD results, four samples were suggested for further XRD analysis and hydrogen sorption testing. These four samples showed the largest volume (based on relative peak intensities) of the desired Zr_2Fe and Zr_3Fe alloys.

These findings represent a positive outcome, in that the combination of attritor milling and subsequent heat treatment to produce Zr-Fe getter materials has the potential to become a high-volume production method that could support the needs of tritium production at SRS.

This page intentionally left blank.

5.0 Acknowledgements

The authors would like to acknowledge funding provided by the The Department of Energy (DOE) National Nuclear Security Administration (NNSA) Plant Directed Research and Development Program at SRS. Initial work on this study was completed by Dr. James Congdon, who retired from SRNL in early 2006. The authors extend their thanks to Xiaodi (Scott) Huang and the Institute of Materials Processing at Michigan Technological University for skilled assistance with the mechanical alloying work, and Arthur Jurgensen and David Missimer at SRNL for expert interpretation of the XRD data.

This page intentionally left blank.

6.0 References

1. Klein, J. E. and J. R. Wermer, "Tritium Stripping in a Nitrogen Glove Box Using Palladium/Zeolite and SAES ST 198TM," *Fusion Technology*, **28** [10] 1532-1539 (1995).
2. Boffito, C., F. Doni and L. Rosai, "The Properties of Some Zirconium-Based Gettering Alloys for Hydrogen Isotope Storage and Purification," *Journal of the Less Common Metals* **104** [1] 149-157 (1984).
3. Nobile, A., W. C. Mosley, J. S. Holder and K. N. Brooks, "Deuterium Absorption and Material Phase Characteristics of SAES St 198 Zr-Fe Alloy," *U.S. Department of Energy Report WSRC-TR-92-557, Revision 1*, Westinghouse Savannah River Company, Aiken, SC (1994).
4. Coleman, M., D. Chandra, J. Wermer and T. Udovic, "Zirconium Iron Disproportionation During Hydriding Reactions in Nuclear Gettering Operations," *Advanced Materials for Energy Conversion II*, edited by D. Chandra, R. G. Bautista and L. Schlapbach. TMS (The Minerals, Metals & Materials Society), pp. 429-435 (2004).
5. Maynard, K. J., N. P. Kherani and W. T. Shmayda, "Nitridation of Zr₂Fe and its Influence on Tritium Removal," *Fusion Technology*, **28** [10] 1546-1551 (1995).
6. Larson, E. J., K. J. Cook, J. R. Wermer and D. G. Tuggle, "Operation of a Tritium Glovebox Clean-Up System Using Zirconium Manganese Iron and Zirconium Two Iron Metal Getters," *U.S. Department of Energy Report LA-UR-CO-3896*, Los Alamos National Laboratory, Los Alamos, NM (2000).
7. Biegel, W., H. U. Krebs, C. Michaelson and H. C. Freyhardt, "Structure Analyses of Amorphous Melt-Spun Fe-Zr-(B,Si) Alloys and Mechanically Alloyed Fe-Zr Powders," *Materials Science and Engineering*, **97** 59-62 (1988).
8. Yartys, V. A., H. Fjellvåg, I. R. Harris, B. C. Hauback, A. B. Riabov, M. H. Sørby and I. Y. Zavalii, "Hydrogen Ordering and H-Induced Phase Transformations in Zr-Based Intermetallic Hydrides," *Journal of Alloys and Compounds*, **293-295** 74-87 (1999).
9. Suryananrayana, C., "The Science and Technology of Mechanical Alloying," *Materials Science and Engineering*, **304-306** 151-158 (2001).
10. Becker, J. E., "Attritor Grinding of Refractories," *The American Ceramic Society Bulletin*, **75** [5] 72-74 (1996).
11. Szegvari, A. and M. Yang, "Attritor Grinding and Dispersing Equipment," *As presented April 29, 1999 at the seminar on Dispersion of Pigments and Resins in Fluid Media at Kent State University, Kent, Ohio*, (1999).
12. Kerr, M. C. and J. S. Reed, "Comparative Grinding Kinetics and Grinding Energy During Ball Milling and Attrition Milling," *American Ceramic Society Bulletin*, **71** [12] 1809-1816 (1992).
13. Suryananrayana, C., "Mechanical Alloying and Milling," *Progress in Materials Science*, **46** 1-184 (2001).

14. Hellstern, E. and L. Schultz, "Glass Forming Ability in Mechanically Alloyed Fe-Zr," *Applied Physics Letters*, **49** [18] 1163-1165 (1986).
15. Hellstern, E. and L. Schultz, "Formation and Properties of Mechanically Alloyed Amorphous Fe-Zr," *Materials Science and Engineering*, **97** 39-42 (1988).
16. Pilar, M., J. J. Sunol, J. Bonastre and L. Escoda, "Influence of Process Control Agents in the Development of a Metastable Fe-Zr Based Alloy," *Journal of Non-Crystalline Solids*, **353** 848-850 (2007).
17. Massalski, T. B. and H. Okamoto, *Binary Alloy Phase Diagrams*, ASM International, Materials Park, OH (1990).

Appendix A

XRD Spectra for the Mechanically Alloyed Powders

